



APPLICATION OF FLAW DETECTION METHODS FOR DETECTION OF FATIGUE PROCESSES IN LOW-ALLOYED STEEL

Zbigniew Hilary ŻUREK

ABSTRACT

The flaw detection techniques have been worked out in order to detect material's non-continuity defects. The demand for endurance and reliability of materials and constructions increases steadily. The flaw detection methods are no longer sufficient, in particular for inspection. It is necessary to learn the degree of material fatigue in a given construction element.

The paper presents the investigations conducted in Fraunhofer Institute (IZFP Saarbrücken) by use of a BEMI microscope (BEMI= Barkhausenrausch- und Wirbelstrom-Mikroskopie or Barkhausen Noise and Eddy Current Microscopy). The ability to detect cyclic and contact fatigue load influences has been investigated. The measurement amplitudes obtained with Barkhausen Noise and Eddy Current probes have been analysed. Correlation of measurement results and material's condition has been observed in case of the eddy current mode method for frequencies above 2 MHz (for contact-loaded material samples). Detection of material's fatigue process (at 80 % fatigue life) in the sample subjected to series of high-cyclic loads has been proven to be practically impossible. Application of flaw detection methods in material fatigue tests requires modification of test methods and use of investigation methods relevant to physical parameters of the investigated material. The magnetic leakage field method, which has been abandoned by many researchers, may be of significant use in the material fatigue assessment and may provide new research prospects.

Keywords: railway transport, non-destructive testing, magnetic diagnostics, material fatigue.

1. INTRODUCTION

Constructional steel due to its excellent mechanical properties is still the basic material used in engineering. A constructional element built of iron alloy can be characterised by magnetic properties, hence it may be inspected by magnetic methods (apart from other known methods). The physical quantities related to the material's structure are magnetic permeability (initial and maximum), coercivity, hysteresis losses, eddy current losses, relaxation losses. The variation in material's permeability at a given steady temperature [1] may be caused by plastic deformation working, heat treatment, specific cooling agent, relaxation of stress and ageing phenomena.

Magnetic methods are used to analyse microstructure and to determine iron alloys phases. They may also be used for the diagnosis of the fatigue process in machine elements.

This paper presents correlation of selected magnetic parameters with material fatigue process and detection tests of fatigue zones by eddy current, Barkhausen and magnetic leakage field methods. A research strategy has been worked out in the Railway Engineering Department of Silesian University of Technology. The test samples were made of the rim of railway wheel set rims steel. Fatigue calibration of the samples has been carried out in Institute of Fundamental Technological Research of Polish Academy of Sciences (IPPT PAN). The structural tests have been performed carried out in the Railway Engineering Department of the Silesian University of Technology. The detection of fatigue changes has been carried out in Fraunhofer Institute in Saarbrücken (Germany), with the help of the BEMI device (Barkhausen Noise and Eddy Current Microscope). The possibilities of generalising magnetic test methods have been determined and pointed out. A magnetic description of the material fatigue process has been proposed. The investigation of the

rolling surface of railway wheel sets has been carried out to document the detection procedures for material fatigue by magnetic leakage field method.

2. TEST SAMPLES

P54T steel used in railway engineering for the rim of wheel -set rims has been used in tests [2, 3]. The following types of samples have been prepared: hourglass-type – for scalable application of cyclic fatigue load (at MTS universal testing machine), and ring-type – for contact loads at AMSLER stand (Table 1). The preparation of the samples is shown in Table 2. The material microstructure compared with the cyclic mechanical loading data is documented in Table 3. The comparison of the material microstructure due to different load histories is shown in Table 4.

Table 1: Types of samples

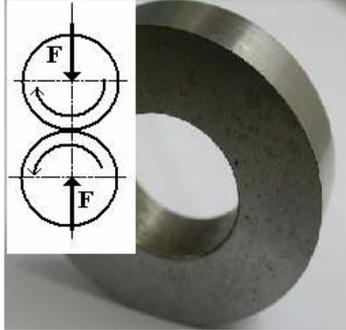
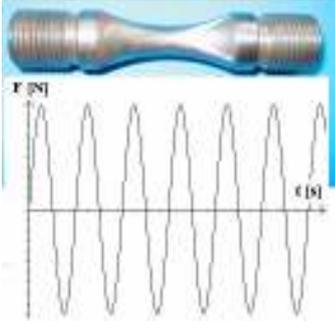
for contact loads at AMSLER stand	for cyclic fatigue load at MTS stand
	

Table 2: Sample preparation process

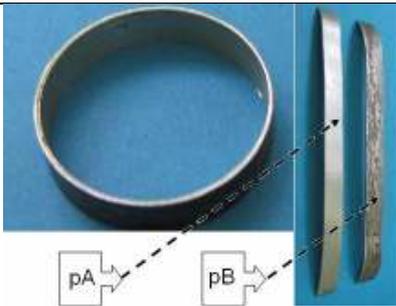
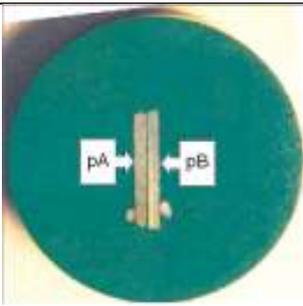
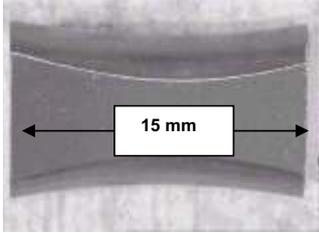
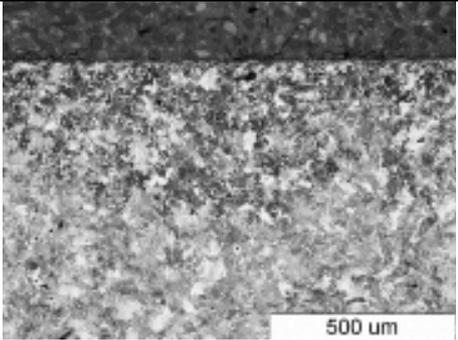
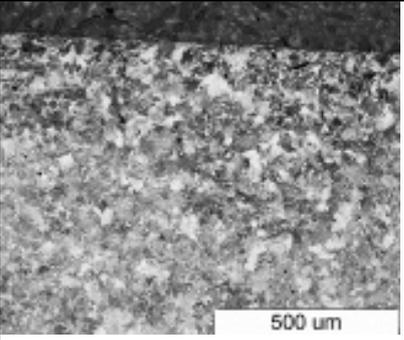
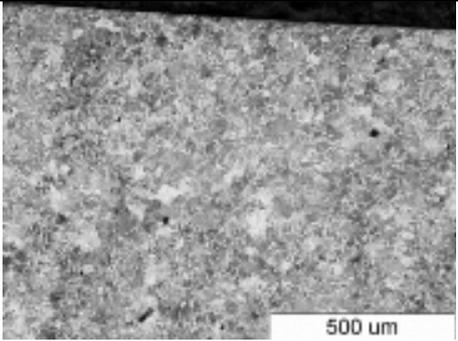
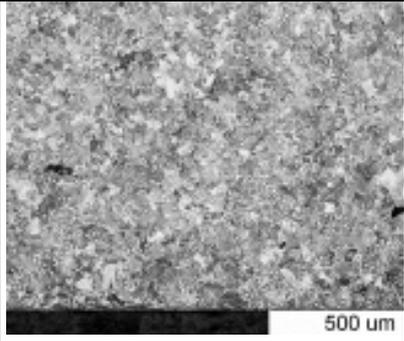
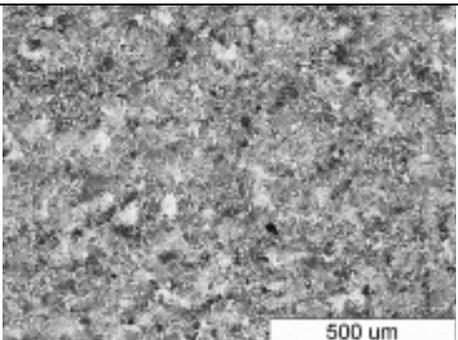
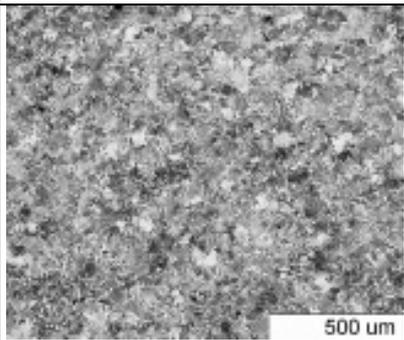
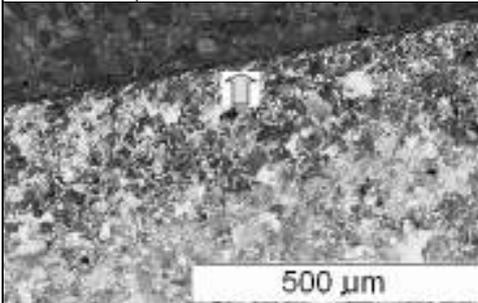
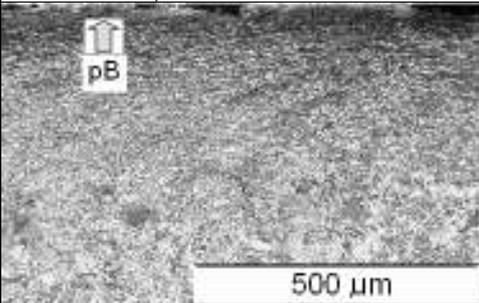
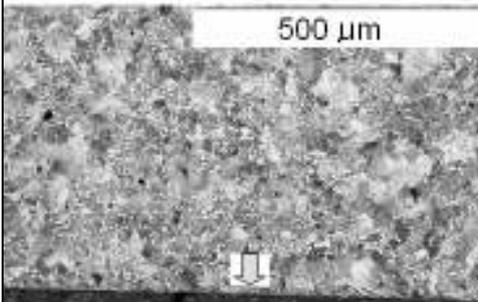
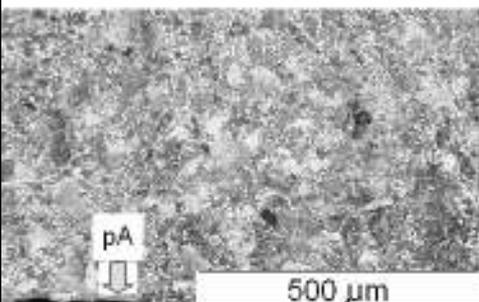
Ring samples – sample preparation process	
	
Hourglass-type samples - sample preparation process	
	

Table 3: Material microstructure vs. cyclic mechanical load cycles

No. of cycles	Hourglass-type samples material structure	
120 000 cycles 78% fatigue life		
80 000 cycles 52% fatigue life		
60 000 cycles 39% fatigue life		

Effects due to fatigue are seen in the final stage of fatigue process. For hourglass-type samples the changes are located irregularly along the percentage reduction of area, in the middle (the narrowest part). The thickness of dark layers observed in the photos does not exceed several-hundredths to several-tenths of millimetre. Samples prepared for microscopic examination (hourglass and ring types both) have been next tested by magnetic methods by the BEMI.

Table 4.: Comparison of material microstructure degradation, material subjected to cyclic and contact mechanical loads

Contact loads Ring sample / AMSLER stand	Cyclic loads Hour-glass sample / MTS machine
 <p>500 μm</p> <p>Material surface after loading</p>	 <p>500 μm</p> <p>Material surface after loading</p>
 <p>500 μm</p> <p>Material surface before loading</p>	 <p>500 μm</p> <p>Material surface before loading</p>
100% sample surface fatigue (flaking)	78% sample surface fatigue

The change of material microstructure in the ring sample is due to contact load. The improper loading leads to laminations and flaking at bigger depths than those shown in the photos. Additionally phase changes take place and this also determines the fatigue process. Deformation of the grains as well as displacements occur and this is one of the basic causes of fatigue cracks emergence.

3. SAMPLE EXAMINATION WITH *B E M I*

The fatigue results are obtained by investigating local changes of magnetisation. Other testing procedures are based on phenomena related to characteristic features of magnetisation process (Barkhausen effect) and changes in electrical conductivity and relative magnetic permeability in eddy-current methods. Figures 1 and 2 show results of scanning the middle part of the surface of the hour-glass sample with the BEMI microscope. The BEMI microscope graphical user interface window is shown in Figure 1, documenting eddy-currents test results at 80000 and 120000 loading cycles, respectively. Figure 2 shows the Barkhausen noise analysis. Each graphical user interface window visualises results of tests of the sample surface and the transducer signal behaviour at a given coordinate indicated in the graphic by the cursor.

According to the change of the sample surface image with the fatigue process correlation has been undertaken for surface slices from disks subjected to tests at AMSLER stand. The samples have been examined before and after contact loading.

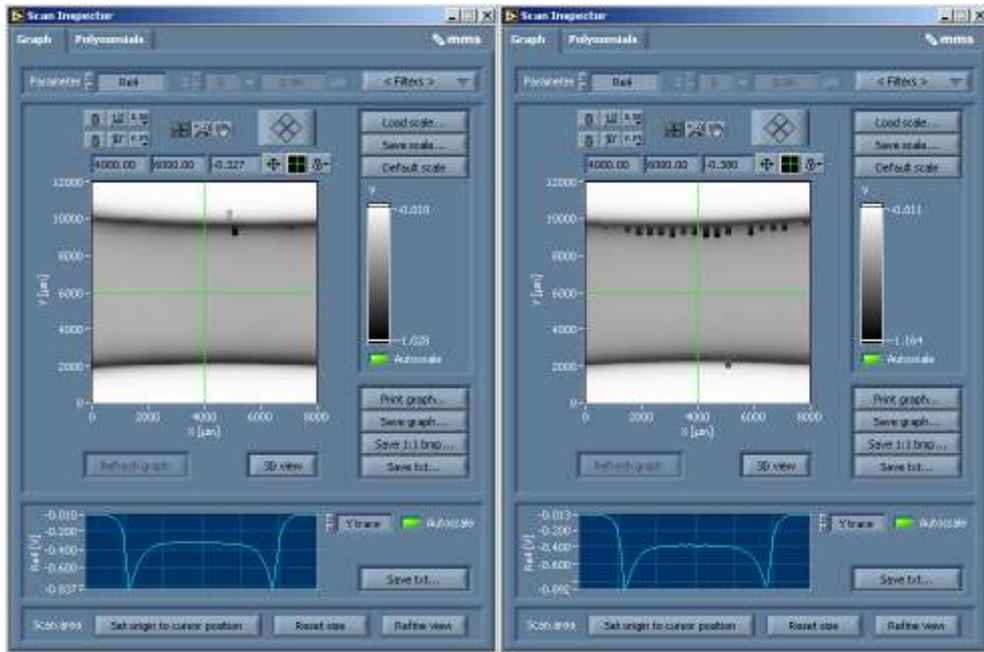


Figure 1: Graphical user interface windows for (2 MHz) eddy-current - test results for samples with 80000 cycles (left), and 120000 loading cycles (right)

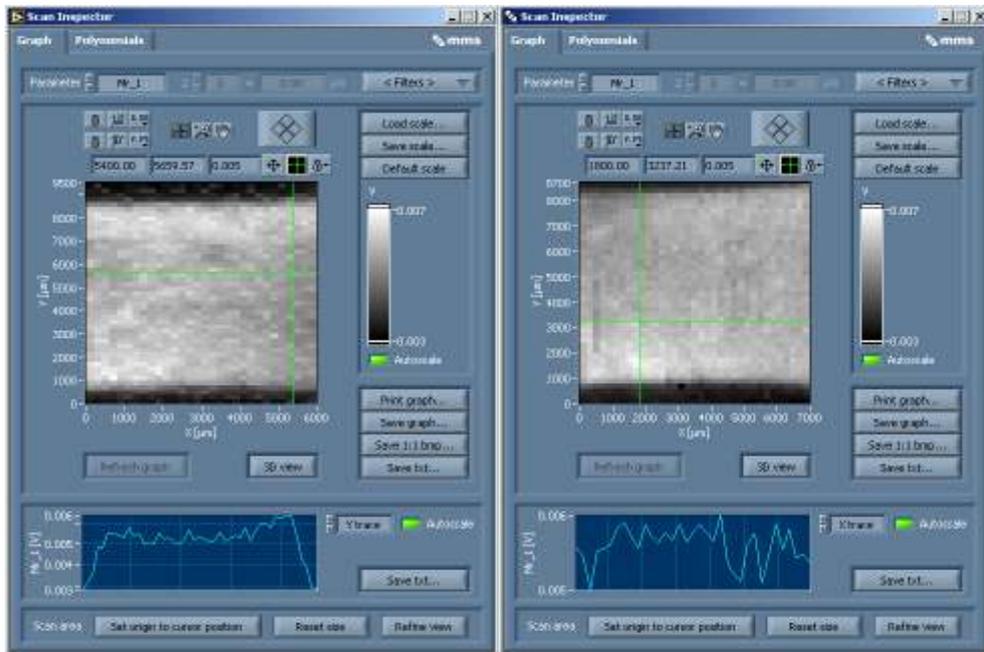


Figure 2: Graphical user interface windows for the Barkhausen noise analysis – test results for samples with 80000 cycles (left), and 120000 loading cycles (right)

Figure 3 shows results of eddy-current scanning of surfaces pA and pB samples for 0,5MHz and 2 MHz.

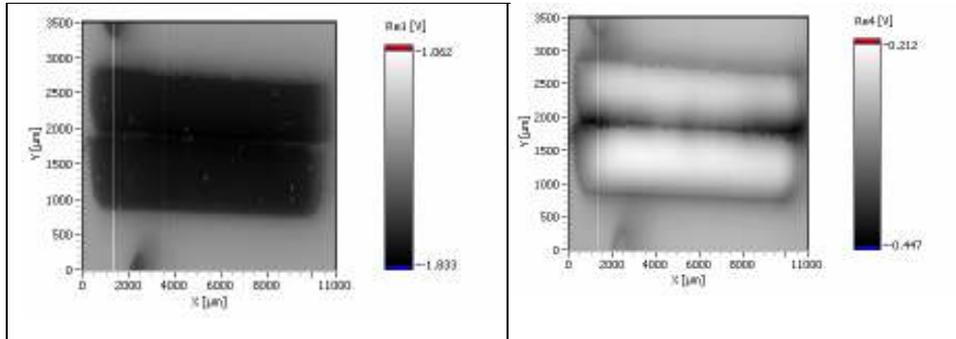


Figure 3: Graphical user interface window information for eddy-current analysis.

Figure 4 shows results of (DH25 = full peak width at 25% of the maximum and M max = Barkhausen noise maximum) the Barkhausen noise scanning analysis of samples pA and pB.

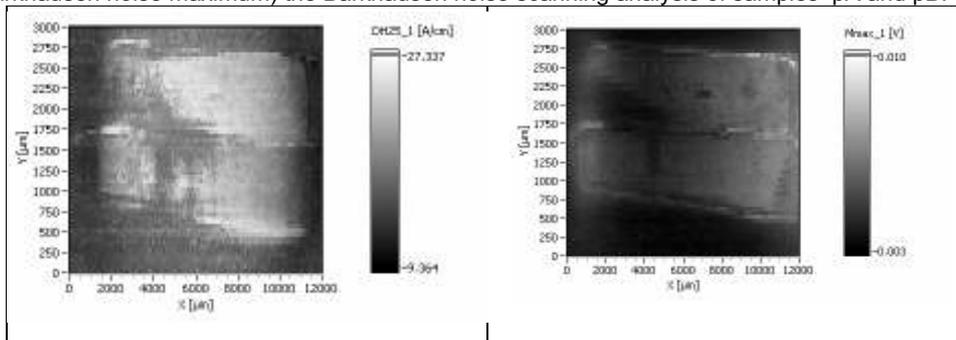


Figure 4: Graphical user interface window information for the Barkhausen noise scanning analysis

4. COMPARISON OF TEST RESULTS

The detection of the fatigue processes at the hourglass sample surfaces was effectively possible for eddy current frequencies greater than 2 MHz, as shown in Figure 5. The number of cycles investigated ranged from a set number n to maximum number n_{max} as a function of probe signal.

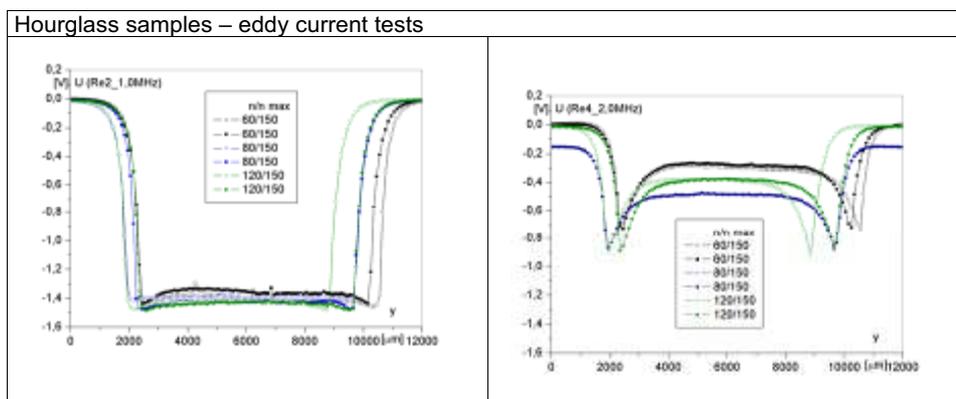


Figure 5: Comparison of eddy current testing
Such a detection was not possible by comparing amplitudes of probe signals during Barkhausen noise testing (Figure 6).

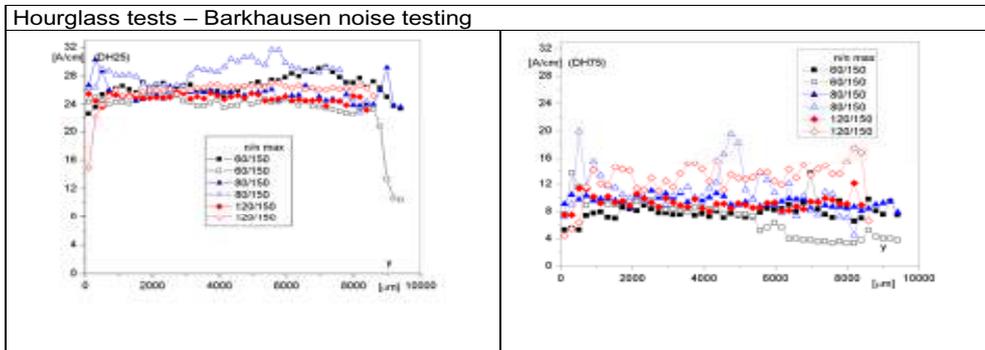


Figure 6: Comparison of Barkhausen noise testing

As opposed to these facts, in case of contact-loaded ring samples a separation between pA and pB samples was possible by eddy current tests for frequencies greater than 2 MHz. However, Barkhausen noise method, made the characterization of the contact-loaded sample possible, as shown in Figure 7.

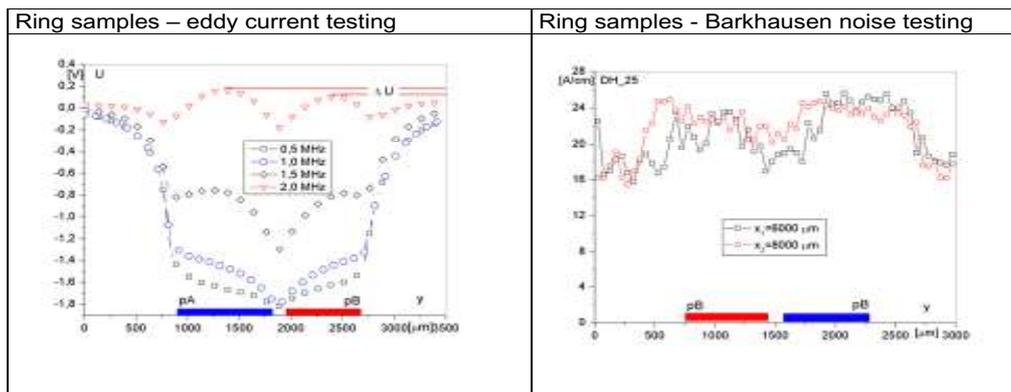


Figure 7: Comparison of Barkhausen noise and eddy current testing

The results prove that only contact-loaded samples may be tested by both eddy currents and Barkhausen noise methods.

5 CONCLUSIONS

The amplitudes of the eddy-current impedance measurement do not reflect the material's condition at 0,5 and 1 MHz frequencies. For frequencies greater than 2,0 MHz eddy-current signals show some differences in the material condition for contact-loaded samples pA and pB. In case of Barkhausen noise method the differentiation between material changes was possible for contact-loaded samples only. The change in material's magnetic parameters (up to 30 per cent) due to fatigue stresses was detected by the eddy current method – the signal increased at approximately the same rate (up to 30 per cent) for both magnetic permeability and coercivity. When the Barkhausen noise method was applied, the results were not so obvious. It must be noted that for the BEMI microscopic inspection the samples were specially prepared. In real life and when the railway wheel set rolling surface is investigated, the detection may be highly effective if leakage magnetic field is measured [4] (Figure 8).

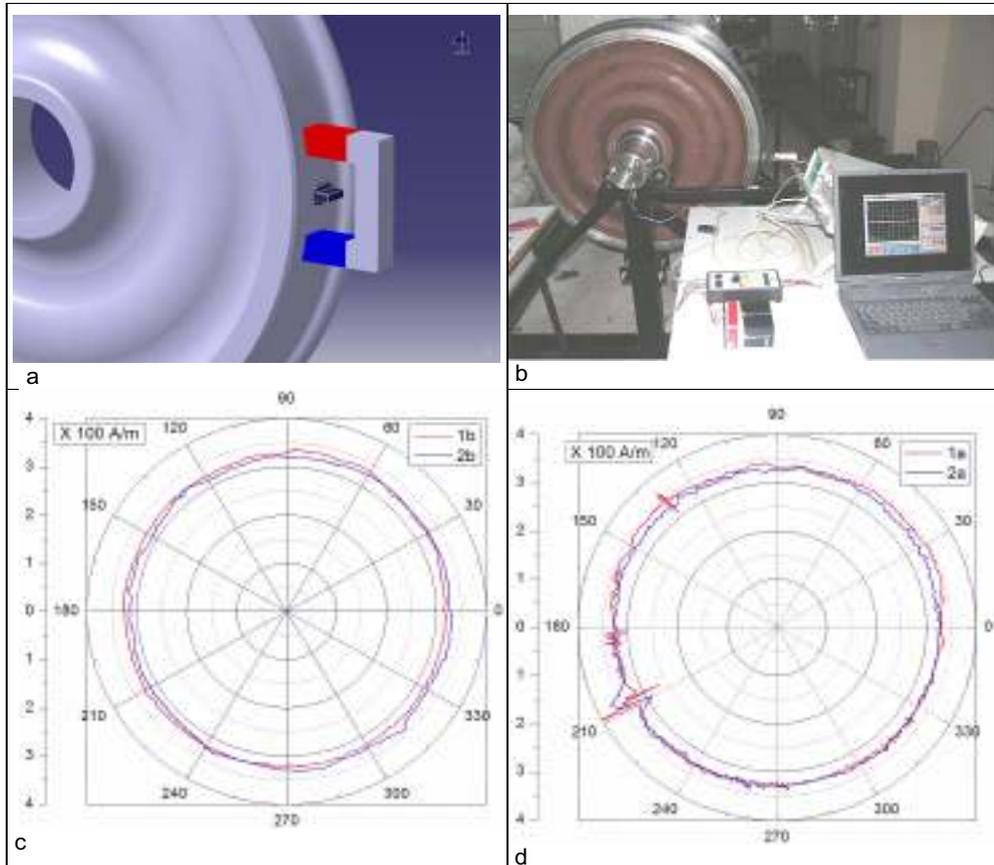


Figure 8: Measurement principle – a, testing – b, leakage magnetic field in a brand-new wheel – c, leakage magnetic field in a damaged wheel – d.

The eddy currents with 2 MHz or higher frequencies only penetrate element's surface near zones. More significant information for subsurface layers may be obtained by analyzing the magnetic leakage field, and in particular, by investigating the tangential component of this field. The BEMI microscope principle is useful in fundamental research; however, in practice (in railway transport service diagnostics) testing of tangential component of leakage magnetic field is a very effective research method, whereas the information on changes in the material's continuity obtained from eddy current or ultrasonic tests is supplementary.

References

- [1] Żurek Z. H.: Magnetic Contactless Detection of Stress Distribution and Assembly Defects in Constructional Steel Element, , NTD&E International 38 (2005) pp. 589-595.
- [2] Żurek Z. H.: Ocena czułości detekcji procesów zmęzeniowych w materiale ferromagnetycznym dla wybranych metod defektoskopowych, X Krajowa konferencja wytrzymałości i badania materiałów, str. 186-193, Kudowa – Zdrój, 20-22 września 2006r. (*Assessment of sensitivity of fatigue processes in ferromagnetic material for selected flaw detection methods – in Polish*)
- [3] Żurek Z. H.: Analiza zmienności parametrów magnetycznych materiału w aspekcie detekcji procesów zmęzeniowych w stalach niskostopowych i niskowęglowych, str. 69-73, X Krajowa konferencja wytrzymałości i badania materiałów, Kudowa – Zdrój, 20-22 września 2006r. (*Analysis of material's magnetic parameters variability related to detection of fatigue processes in low-alloyed and low-carbon steels – in Polish*)
- [4] Żurek Z. H.: Magnetic monitoring of fatigue process of the rim material of railway wheel sets, NDT&E international, 39 (2006), pp. 675-679.