

Hand Held Ultrasonic Sizing of Stress Corrosion Cracking

Robert GINZEL, James PENNIE, Eclipse Scientific Products Inc, Kitchener, ON, Canada
Jim MARR, Marr Associate Inc., Calgary, AB, Canada

Abstract. Stress corrosion cracking (SCC) is now globally recognized by pipeline operators as a significant threat to the safe and efficient operation of their systems. Onshore natural gas, oil and refined products line pipe steels have all been susceptible to this form of environmentally assisted cracking, which can develop as either low or high pH SCC. Over the years, the pipeline industry has developed several non destructive examination (NDE) techniques to identify, document and evaluate the severity of a SCC indication, including magnetic particle inspection (MPI) and ultrasonic (UT) sizing.

While MPI can locate and assess the surface dimensions of the cracks within the SCC indication, measurements of crack depth within the colony have not been as easily obtained under field conditions. Researchers have been developing field based hand held ultrasonic (UT) sizing techniques to determine the actual crack depths. The UT determined SCC crack depths are incorporated into engineering assessments and crack growth models (used in risk algorithms), potentially enabling operators to effectively address, monitor and thus manage this time dependent threat. This paper will discuss our experiences since the mid 1980's with UT crack sizing, the techniques that are available in the industry, the limitations that still exist, and the benefits of using a new UT assessment transducer to assess SCC crack depths.

Introduction

Sizing cracks has been, and continues to be, a hotly debated topic within the Non Destructive Examination (NDE) industry. There are many sizing methods presently available and emerging technologies will continue to advance the accuracy and reliability of crack sizing. Limitations due to erroneous application, operator skill and experience levels can affect the usefulness and the success rate of certain techniques presently available in the market place. It is critical that technicians, company managers, engineering staff and the end customer understand the limitations of a specific UT technique, its reliability and comparative options that are available to address a potential SCC integrity threat. The primary purpose of this paper is to recap existing UT techniques and unveil to the industry the NSDS probes used to size external SCC on line pipe steels.

Nomenclature

Stress Corrosion Cracking (SCC) Cracking induced from the combined influence of tensile stress, susceptible steel and a corrosive environment.

Diffraction When an ultrasound wave is incident at a linear discontinuity such as a crack, diffraction takes place at its extremities (i.e. crack tip). The study of this

phenomenon has led to the development and use of time of flight diffraction method for crack sizing.

Time of Flight Diffraction (TOFD - Delta Technique) This technique uses the diffracted signals from the crack extremities, as compared to conventional methods of relying on the amount of energy reflected by the extremities of the discontinuities. The transducer elements are positioned either in the same housing or separate housings but will be angled towards the other.

Bimodal or Multimode Two or more modes (i.e. longitudinal and/or shear waves) transmitted into the material at the same time, each mode being used for a specific purpose.

A-Scan Data display in which the received pulse amplitude is represented as a displacement along one axis (usually the y-axis) and the travel time of the ultrasonic pulse is represented as a displacement along the other axis (usually the x-axis).

C-Scan A two dimensional graphical presentation in which the discontinuity echoes are displayed in a plan view on the test surface.

B-Scan A two dimensional graphical presentation in rectangular coordinates, in which the travel time of an ultrasonic pulse is represented as a displacement along one axis, and transducer movement is represented as a displacement along the other axis.

Dual Transducer A method of UT that uses two transducers, one transmitting and the other receiving, often referred to as *pitch and catch*.

Tandem Configuration Tandem configuration refers to a transducer setup (transmit and receive one ahead of the other) with the elements facing the same direction.

Signal to Noise Ratio The ratio of desired sound to undesired background noise, measured in decibels (dB)

Background Experiences

Requirements for SCC sizing have changed over the years from performing a simple visual assessment of the SCC colony to using complex phase array UT based systems. Determining crack depth to address severity of the colony was initially based on length to depth ratios. These ratios were not consistent and were highly variable between both individual colonies and the two types of SCC (i.e. low and high pH SCC). The industry required quantitative information about flaw size to serve as an input to fitness for service, fitness for purpose and/or engineering critical assessments.

The ease of measurement capability and reliability of UT results effectively enabled the engineer to determine the remaining life of a defect. These UT based measurements assisted in establishing critical crack lengths and depths to assist in determining the predicated time to failure of defects based on a quantitative, not qualitative analysis.

Concurrent to UT, several other NDE developmental technologies are becoming available such as Eddy Current (ET) to measure crack severity. Arguably, at this point in time, UT provides the most mature, robust and reliable technique to obtain crack depth measurements given the field conditions of most onshore pipelines.

Considerations

Items that should be considered when selecting the transducer and subsequent measurement approach include:

- Crack location and other potential defects (i.e. external corrosion) associated with the material or manufacturing process

- Material properties, grain structure and signal attenuation, and
 - Pipe physical configurations including thickness, radius, and geometrical considerations
- All technicians should be following an analytical process that addresses the proposed application and applicable UT tools. In some cases UT inspection may not be suitable and another more appropriate NDE discipline should be selected.

Available Sizing Technologies

Utilizing UT techniques, crack depth is determined through the analysis of the waves reflected, transmitted or diffracted by the crack. It should be recognized that some basic UT techniques are used to qualify general defect characteristics or to convey that a defect is actually present in the material being inspected.

Until 1995, no transducers were specifically developed for the detection and sizing of OD breaking SCC. The primary categories of transducers and techniques utilized for ultrasonic crack detection and sizing techniques are briefly discussed below:

A) Conventional Ultrasonic Transducers (using the Amplitude Drop Technique)

Conventional ultrasonic transducers are commonly referred to as shear, unfocused and focused probes.

Conventional probes in conjunction with newer versions of ultrasonic instruments can be very capable of measuring some orientations of SCC or SCC like colonies, but cannot be effectively used in all circumstances. Ultimately the major problem using these traditional tools is isolating specific cracks in an attempt to size due to the close proximity of individual cracks relative to each other within the colony.

B) Amplitude Comparison

An amplitude comparison technique is probably the oldest known UT measurement method and is applicable in certain situations. This technique usually involves the analysis of defect echo amplitudes to echo amplitudes from known reflectors from calibration blocks or reference pieces.

When the defect dimensions are less than the beam dimensions (see Figure 1), lateral probe movement from a maximum amplitude results in immediate reduction of signal amplitude. Importantly, the probe displacement is more a result of beam dimension than defect dimension. This is more pronounced as the ratio of beam width to defect width increases.

Typically the length of an SCC colony is determined by a visual technique either Magnetic Particle Inspection (MPI) and can be verified using a UT amplitude drop method provided that the indication is wider than beam spread. The vertical extent of the crack is not as easily obtained. When determining the vertical extent of a crack, the beam spread and amplitude of the corner reflector can significantly exaggerate the depth of the crack.

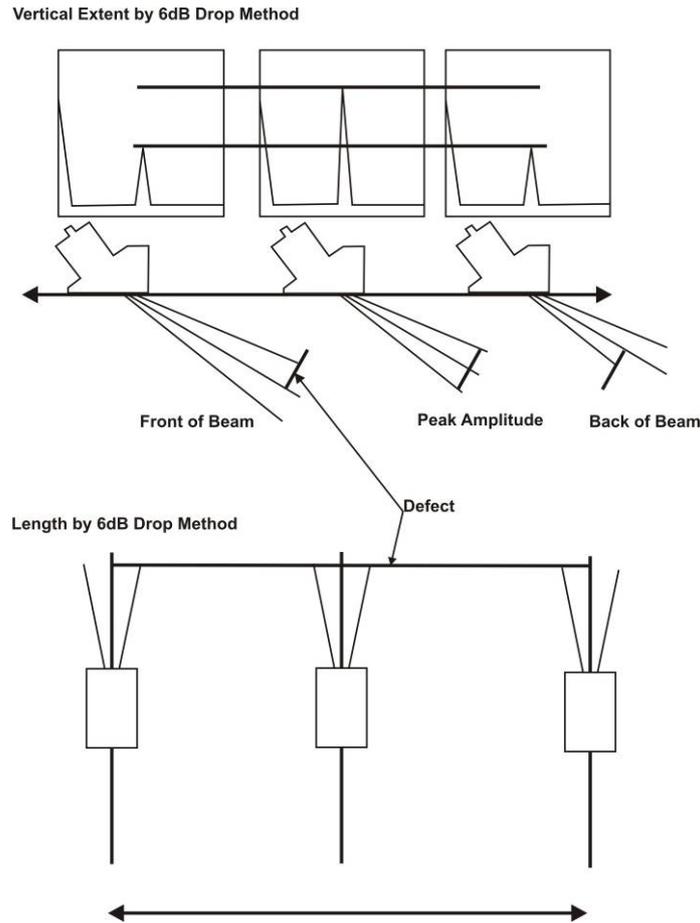


Figure 1 Amplitude Comparison

C) Multibeam and Multimode Transducer Techniques

Usually there is a large uncertainty in crack depth measurements by utilizing the amplitude drop technique (see section A). A series of multibeam and multimode transducers were developed and have demonstrated an improved performance in the sizing of intergranular stress corrosion cracks (i.e. also known as high pH SCC) using time of flight measurements. The multibeam and multimode transducers combine the capabilities of shear and longitudinal wave transducers into a single search and sizing unit. These transducers capitalize on the multiple interactions of the transmitted shear and longitudinal waves with the crack face and its extremities.

When applied to SCC, this technique is identified as “same side sizing” of cracks. The transducer results are influenced by both wall thickness and pipe curvature. These types of transducers were generally designed and suited to the detection and sizing of ID breaking, mid-wall, or very deep cracks.

D) High Angle Dual Element Transducer Techniques

Another technique is the use of dual element transducers with a range of known configurations such as dual (side by side) and tandem (transmitting element ahead or behind receiver).

Dual element transducer configurations, those with transmitter and receiver side by side, are very common and date back to the very early ultrasonic inspection days in the 1940's.

Dual normal beam, shear and longitudinal angled beam applications are all very popular within the NDE UT industry.

Figure 2 illustrates the high angle technique that essentially produces the same wave components as the creeping wave technique (see Figure 4) and can also employ the same transducers for the same application. When using these transducers for OD connected cracks the interpretation and skill of the operator are the primary tools for resolving the depth of the crack. Identifying a crack tip by moving the transducer away from the flaw is a difficult under ideal conditions, when a crack is multi faceted or within a colony as is the case for SCC accuracy that can be achieved is no longer acceptable for thin wall material when other technologies are more reliable and less dependent on the technicians interpretive skills.

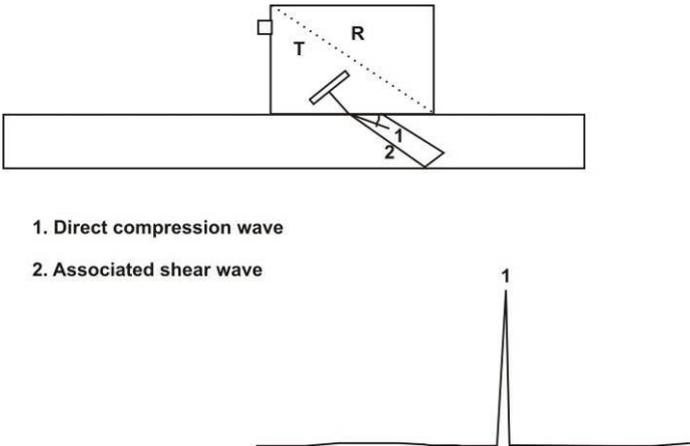


Figure 2 High Angle Longitudinal Wave Technique

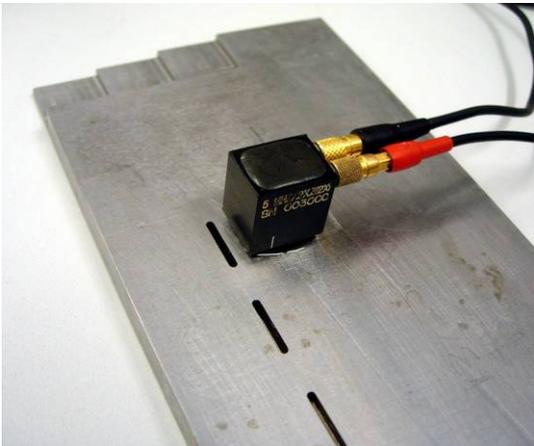


Figure 3 FAST Transducer on ETW Type II Calibration Plate

Improvements in piezoelectric materials such as the development of composite elements have again improved signal to noise ratios and increased the effectiveness of this style of transducer. By optimizing the design, additional enhancements have been made to beam dimensions, pseudo focusing, and, in some cases, the ability to damp signals. The option to tighten or improve the beam dimension in combination with reduced number of signal cycles has improved the performance of this technique for certain applications.

A recent application of dual element high angle technique was introduced to the industry as the Flaw Analysis and Sizing Transducer (FAST) technique.

The transducers used in the application of the FAST technique were initially designed to detect and provide depth approximations of a defect in stainless steel components from the inside diameter or opposite surface from which the work was being performed. The presence of the shear wave is of concern during calibration and sizing. Mode conversion of this signal may lead to misinterpretation and false signals could potentially be recorded. Limited operator training and overall experience can be a major concern when using this technique.

E) Bi-Modal Technique

Bimodal methods typically employ the tandem configuration (one element positioned in front of the other and angled away from the other see Figure 3). This method is normally used for sizing cracks ranging in depth from 30-70% through wall and the measurement usually originates from the ID.

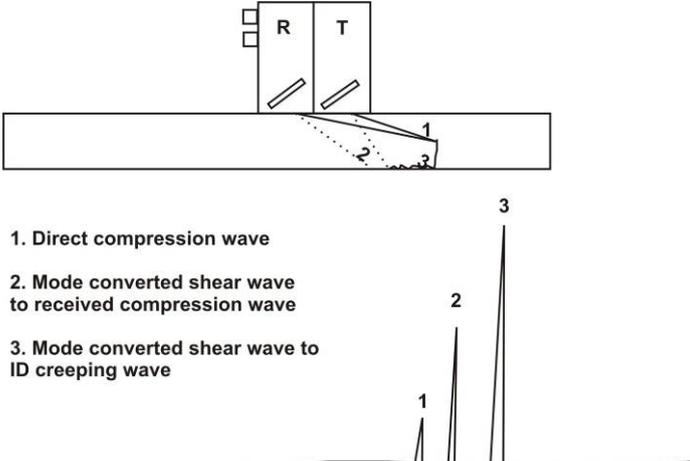


Figure 4 Bi-Modal Tandem Configuration

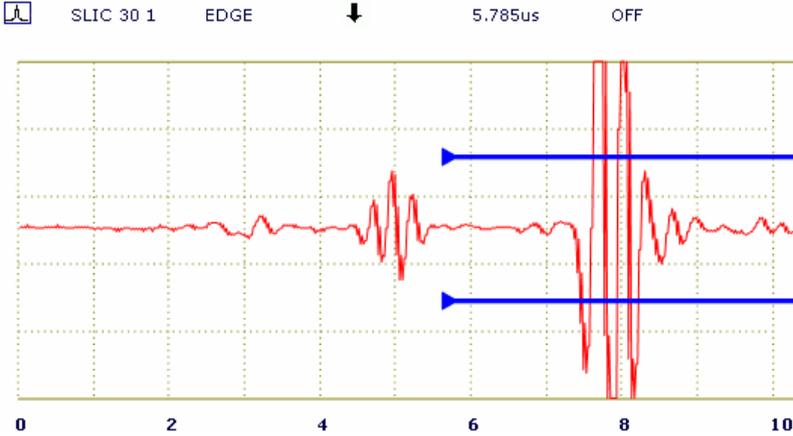


Figure 5 Actual SLIC 40 Signals - EPOCH4 Plus

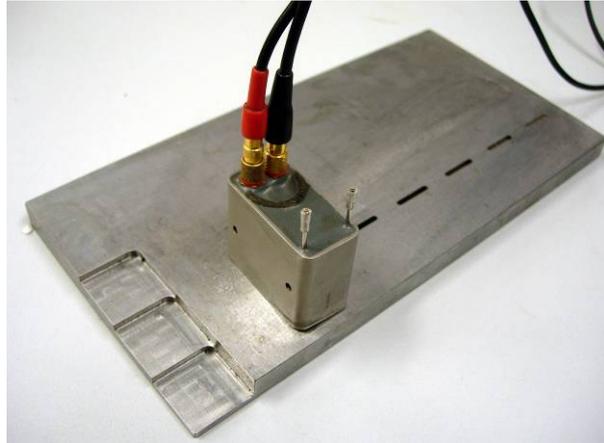


Figure 6 SLIC 40 Transducer on ETW Type II Calibration Plate

F) Creeping & Guided Wave Techniques

These techniques are normally used as “indicators” to detect the presence of a defect and convey a general awareness of the location of a defect (i.e. top third of material, middle or opposite wall) to the technician. Dual shear and dual longitudinal transducers, including dual multimode units such as the creeping wave probes (see Figure 4), have become popular for several reasons. The popular 30-70-70 (VSY) transducer was originally intended for stainless steel applications, but while it can be applied to carbon steel with some success, it should also be classed as a preliminary detection and/or indicator technique.

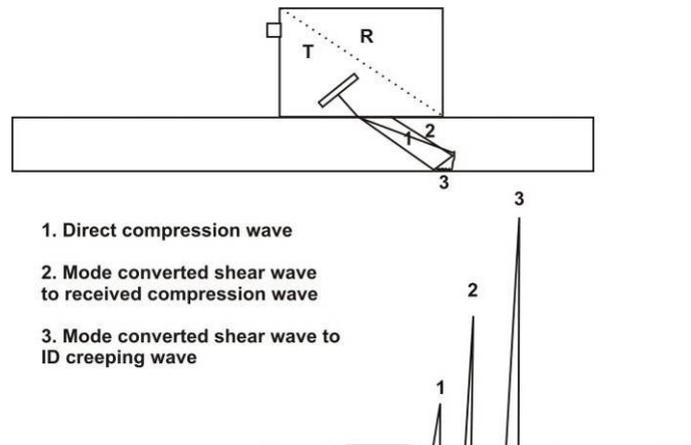


Figure 7 Typical Creeping Wave Transducer with Signal Components



Figure 8 Actual VSY 70 Signals - EPOCH4 Plus

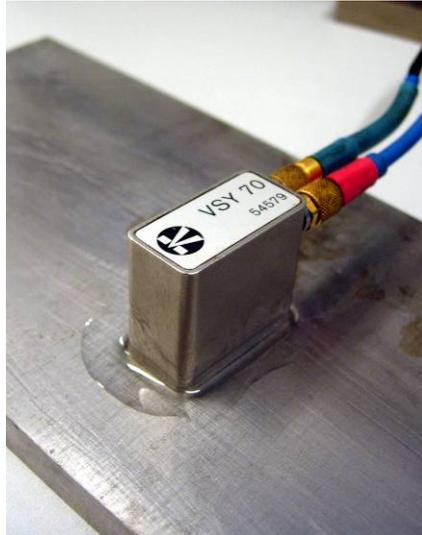


Figure 9 VSY 70 Transducer on ETW Type II Calibration Plate

Crack depths can occur at all levels within the pipe material and can be at almost any orientation. They also freely pass through boundary lines (i.e. such as heat affected zones) or even turn to follow a construction or metallurgical boundary.

This technique would not be normally considered for SCC sizing based on our experiences. It has been included because it is a recognized technique and is mentioned in the literature as a crack sizing technique.


G) Diffraction Techniques

There are two known techniques used within the industry regarding diffraction techniques, simply identified as forward and back diffraction. Diffraction techniques utilize the principles of time of flight diffraction (TOFD). Both techniques are described below. Figure 5 schematically illustrates a forward diffraction technique.

G.1) Forward diffraction

TOFD is a high speed volumetric technique that can provide location and vertical extent of a defect. Although traditional configurations are known to be weak at detection and sizing of near surface defects, such as SCC located on the transducer side. Various techniques can be applied to improve inspection in this specific region including a double skip, and “W” approach.

The TOFD technique continues to gain recognition and improvements will continue for both transducers and analysis techniques. This approach has several characteristics that make it very user friendly although technician experience is still a significant factor in its success.

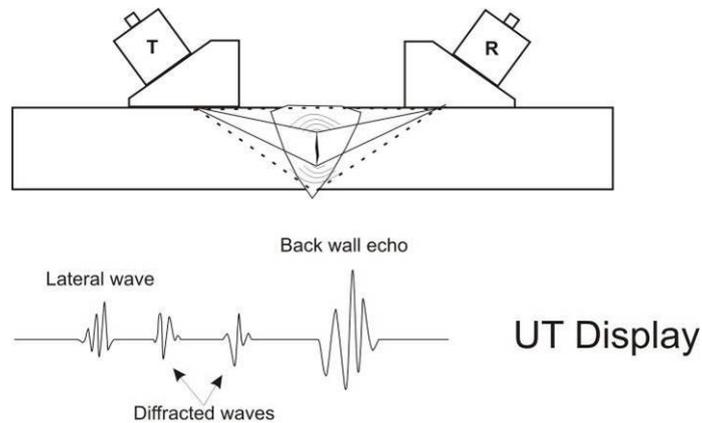

Typical pattern of pulses from internal flaw
 Figure 10 TOFD (Delta) Transducer Arrangement

G.2) Back Diffraction

When using this technique, the transmitter and receiver are positioned ahead and/or behind each other. This positioning can produce a wide range of options related to the detection and sizing of defects. These options include using similar angles for the transmitter and receiver, or varied transducer angles.

In some cases, combinations are used that include multimode options such as coexisting longitudinal and shear waves. Signals can be detected by the placement of the receiver to catch, direct or skip signals, or if seeking only one specific signal mode, by placement of the receiver directly above the defect. Actual signal characteristics would be further divided into the recognized conventional shear and longitudinal waves with bi-modal recognized as the combination of these two wave modes.

G.3) Satellite Pulse Technique (SPT)

This method is used for sizing shallow cracks ranging from approximately 5-35% through wall. This method utilizes the arrival time of the signal from the tip of the crack to determine crack depth. To simplify this process the instrument is calibrated where each screen division corresponds to a particular flaw depth.


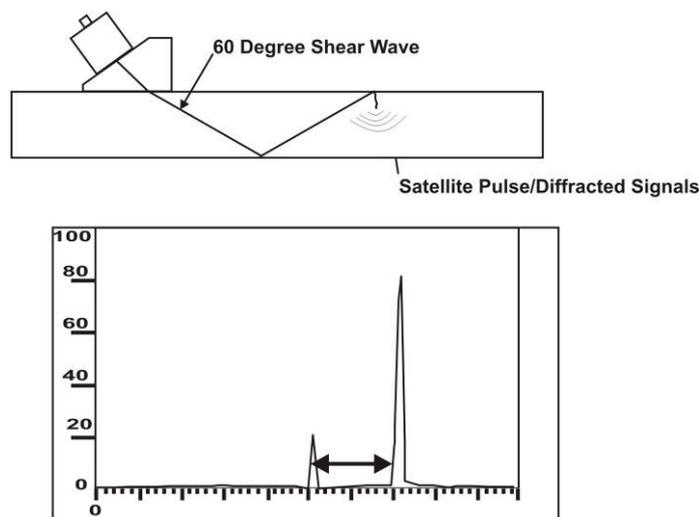


Figure 11 Illustration of Satellite Pulse Techniques SPT

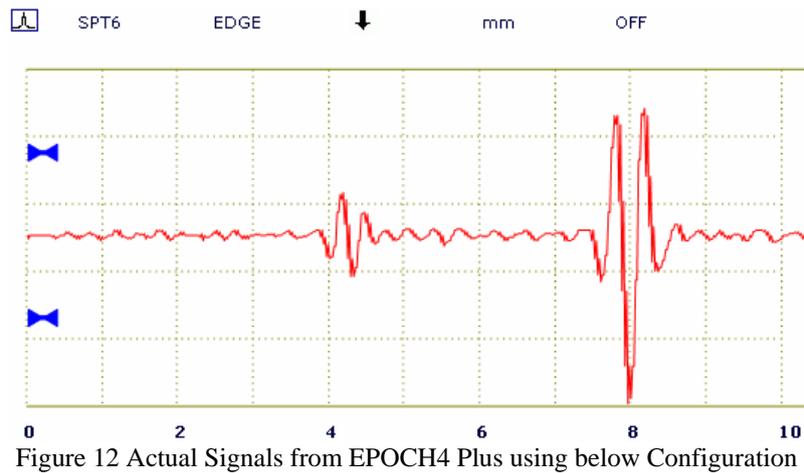

The above signal shows the corner trap at the full skip at the 8th division and the signal from a 50% through wall notch at the 4th division.



Figure 13 0.25"/10MHZ KBA Highly Damped Transducer with 60 Degree Wedge on the ETW Type II Calibration Plate

The SPT technique uses back diffraction. The 60 degree shear wave is targeted at the corner trap, and this causes the crack signal to oscillate. The oscillation travels down the crack and induces a diffracted signal in the test piece. This diffracted signal is received by the transducer and displayed on the instrument as arriving earlier in time than the corner trap signal. Other back diffraction techniques designed to collect the diffracted signals may use a separate receiver element to collect the diffracted signals (i.e. NSDS transducer).

Field Experiences and SCC Sizing

History

Utilizing the best technology for the period and through concurrent field and bench top testing, subsequent analysis and refinement has caused our inspection of SCC to become more reliable and consistent. Our experiences and access to sizing data as well as pre and post mitigation of indications, has improved our confidence to a level where we are exclusively utilizing Near Side Detection and Sizing (NSDS) Transducers.

The NSDS probe is a transducer that has a similar design to some of the other tandem configured transducers types mentioned earlier; Sigma and SLIC are two similar tandem

configurations. The difference, based on our experience using the NSDS probe is the signal strength and the position and angles of the transmission and receiving elements of the transducer. Most importantly, the NSDS was designed specifically for detection and sizing of both linear and SCC indications on line pipe steels (see Figures 14, 15, and 16).

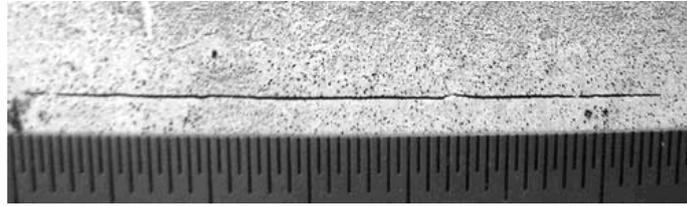


Figure 14 Linear Indication along Electrical Resistance Weld (ERW)

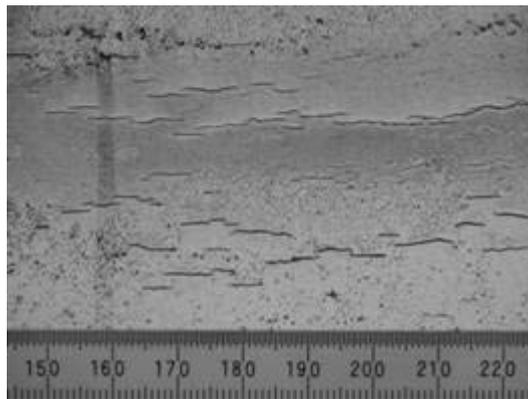


Figure 15 Typical Low pH SCC Colony

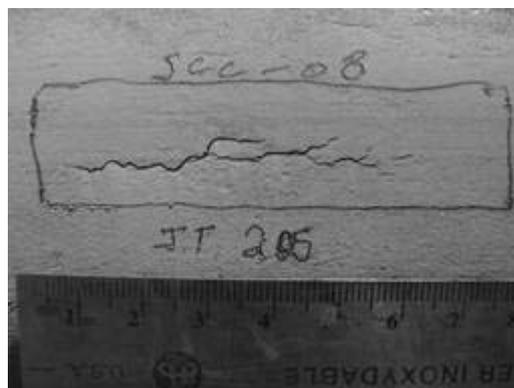


Figure 16 Typical High pH SCC Colony

Near Side Detection and Sizing Transducer (NSDS)

The NSDS H-series transducer design utilizes two piezoelectric elements in a tandem configuration that enable a time of flight tip diffraction measurement to be obtained from an indication. Figure 17 illustrates the path travelled by the sound beam when it is used to same side size crack like defects. To create this beam path, the transmitting element (Tx) is positioned at the rear of the transducer and set at an angle creating a near 70° longitudinal wave. The receiving element (Rx), located at the front of the transducer, is positioned to receive signals at shallow angles (i.e. $<15^\circ$). The design allows the signal to be concentrated on the tip of a SCC indication resulting in a strong, clear response.

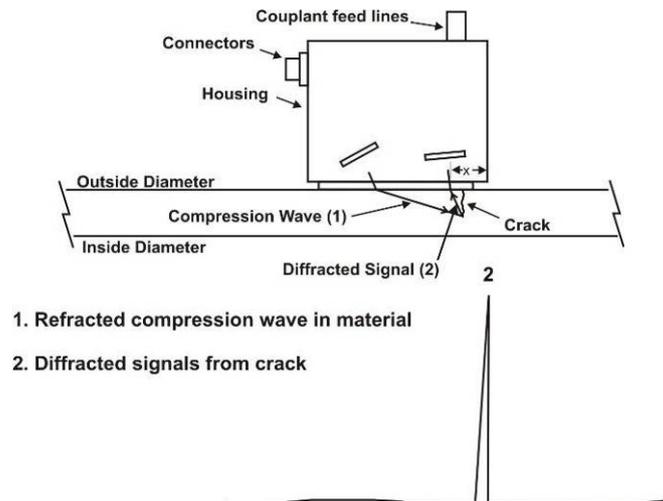


Figure 17 Illustration of NSDS Operation Principal

As illustrated in Figure 17, the transducer must be positioned above the defect to allow recovery of the signal. The exit point of the returning signal, labelled as "x" in Figure 10, is located approximately 9mm back from the front of the transducer. The exact position of the exit point will vary depending on the defect depth being sized.

The NSDS H-series transducer is designed for same side sizing of surface breaking defects in carbon steel utilizing piezoelectric elements that provide an optimum response. Wedge design, piezoelectric element selection, and element separation are all configured to provide clean, concise signals with an enhanced signal to noise ratios. The NSDS H-series transducers are capable of sizing defects as shallow as 0.5mm in material as thin as 4mm or defects up to 15mm in depth for thicker materials. Defect sizing at even greater depths is also possible with alternative transducer designs.

The NSDS H-series transducers are designed to work with almost any UT instrument and can be used in a manual or automated inspection format. The NSDS H-series transducer is 38 by 26 by 40 mm (1.5 by 1.0 by 1.6") and includes 4-40 mounting holes located in the stainless steel housing along with couplant lines for automated inspection formats (see Figure 18). When sizing with the NSDS transducer in a manual format an RF waveform presentation or phase specific presentation is recommended. For automated inspection formats, the collection of digitized waveform data is recommended with the option of monitoring the time of flight data and amplitude data.



Figure 18 NSDS Transducer

The transducer was designed around arrival times (segregation of signals) and multiple inspection purposes (to detect and size internally generated SCC as well as other surface breaking indications). Sound waves returning from the other transducer modes arrive much "farther apart" in time than that of the diffracted signal. This time separation can be as much as two micro seconds. This allows for easy interpretation and less confusing signals from which the operator will extract data pertaining to the defect depth.

Modified Applications of the NSDS Probe

SCC failures have been reported on pipeline diameters as low as 20 cm. It is also our experience that there are many more operators with smaller diameter lines that need to address the SCC threat. The Quest Sizing Stage (see Figure 19) was designed for accurate sizing of SCC indications on smaller diameter pipelines using the NSDS probe.

The sizing stage eliminates the need to contour the transducer, which renders it useless for a range of different pipe diameters. The stage approach utilizes a single transducer that can be used on all applicable pipe diameters, and only the lens contained within the stage is required to be changed.

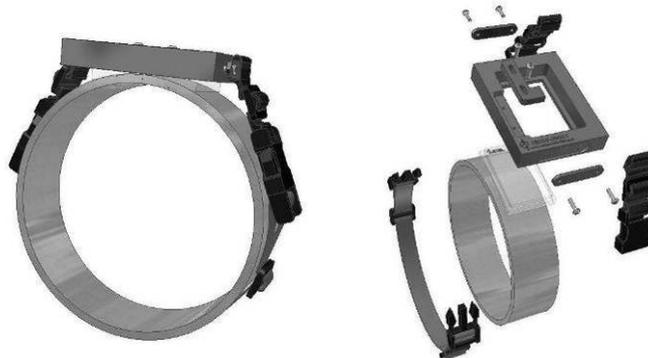


Figure 19 Quest Sizing Stage

For large diameter pipelines, the curvature becomes less necessary to achieve accurate and reliable results. Therefore a similar probe contour can be used for different diameters within a specific range. For example, probes that are not purposely contoured are successfully being used on 40 cm diameter lines and greater.

NSDS Calibration

Calibration is a critical component for most UT applications. Calibration of the NSDS probe can be performed in several ways. Based on our experiences, we normally complete the calibration utilizing a representative “pipe material” plate with side drilled holes (SDH) of varying depths. The plate serves as a calibration sample for technicians performing inspection on the same material as the line pipe to be investigated.

This representative plate sample is utilized to generate a conversion chart relating signal time to corresponding depth using a B-scan. The following data (illustrated in Figure 20) was obtained from SDHs that had been introduced into a sample plate containing SCC (see Figure 21).

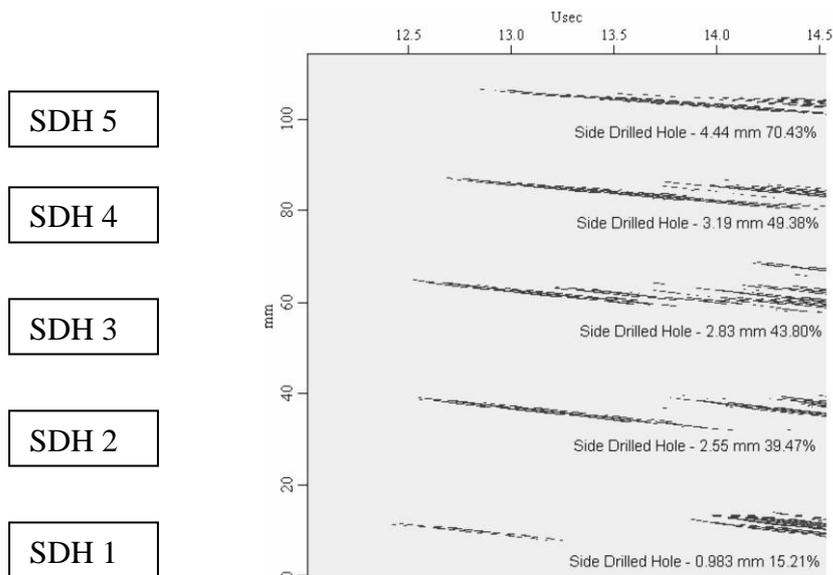


Figure 20 B-Scan of Calibration SDH

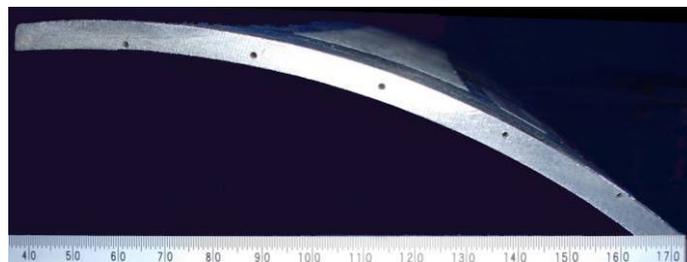


Figure 21 Calibration Sample with Side Drilled Holes

A semi-automated B-Scan of the SDHs in the plate sample was obtained using the NSDS transducer. From the B-Scan (see Figure 20), time data was collected for each SDH and the data was tabulated (see Table 1) and graphed (see Figure 21) with the actual depths to generate a conversion calculation. The graph can also be used to obtain direct readings.

SDH ID	Time (μsec)	Actual Depth (mm)
1	12.590	0.983
2	12.924	2.55
3	13.076	2.83
4	13.302	3.50
5	13.798	4.55

Table 1 Data Extracted from B-Scan

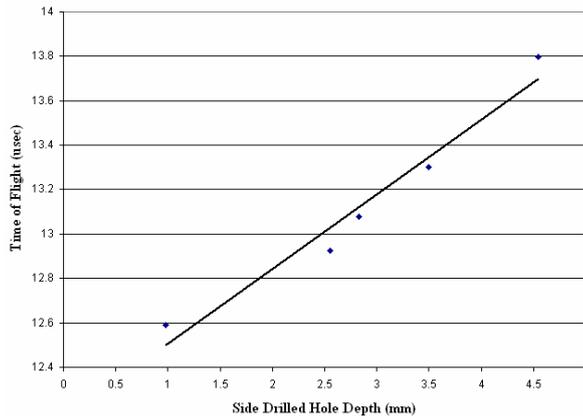


Figure 22 Time to Distance Conversion Chart (Table 1 Data)

Interpretation Reliability (Field to Bench Top)

Over the past several years, this accurate and consistent sizing method has demonstrated excellent correlation between ultrasonic measurements and crack depths removed by buffing. In 1997 the CEPA (Canadian Energy Pipeline Association) published a Stress Corrosion Cracking Recommended Practices which includes Appendix 6 pertaining to the manual SCC sizing using this technique.

NSDS Sizing Results Compared to C-Scan Data

To address variable depths to the actual crack we have included a test result relating UT NSDS measurements to the appearance of the SCC colony. Table 2 identifies the x,y locations within the SCC colony where the NSDS C-Scan measurements were taken. The measurements taken from the C-Scan were recorded in µsec and converted to mm by calculating the materials longitudinal velocity. The NSDS measurements compare well with the opposite wall C-Scan data, with the NSDS overcalling the crack depths by 0.2mm (3.1%).

ID	Measurement Coordinate (Axial & Circumferential) Sample	C-Scan Data Time & Depth		NSDS Measurements (mm)
		µsec	mm	
A	40.8 /22.598	0.840	2.51	2.7
B	50 /22.598	0.664	1.99	2.2
C	59.77 /22.79	0.904	2.70	2.9

Table 2 NSDS Results Compared to C-Scan Data

The C-Scan (see Figure 23) data summarized in Table 2 was obtained using software and scanning the sample from the side opposite the indication in an immersion tank with a copolymer transducer for improved resolution. Figure 23 illustrates a 1:1 comparison of the C-Scan display and the actual crack surface profile.

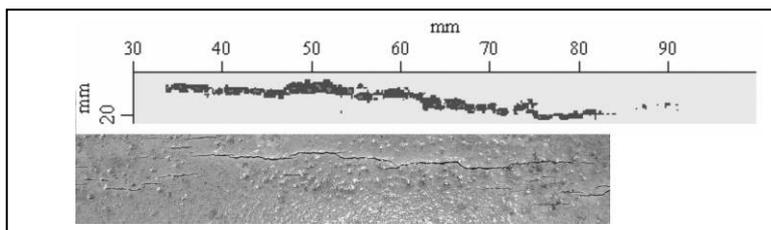


Figure 23 C-Scan of SCC indication

Future UT Developments Using NSDS Technology

Currently we are working on using the NSDS technology in combination with other instruments that will acquire and store data digitally, with the ability to view the data in multiple views (i.e. A-Scan, B-Scan, and C-Scan). Presently some instruments have limited viewing ability and others are simply too large and not suited for the field. The anticipated benefit will be that data can be reviewed and analyzed in greater detail in the field, as well as allowing a permanent record of the feature to be saved. The option of defect monitoring to establish accurate growth rates is also possible, although in most cases not realistic except for in a laboratory environment.

Existing successful multiple diffraction approaches are now being applied using the new technology potential of phased arrays. Although the application to thin wall pipe line is still being researched we have looked into applying the NSDS technology to phased array. The application has had promising preliminary testing and the new probes are presently being designed to address this need. Figure 24 presents a scan that was performed using a 32 element phased array transducer and a one axis sector scan

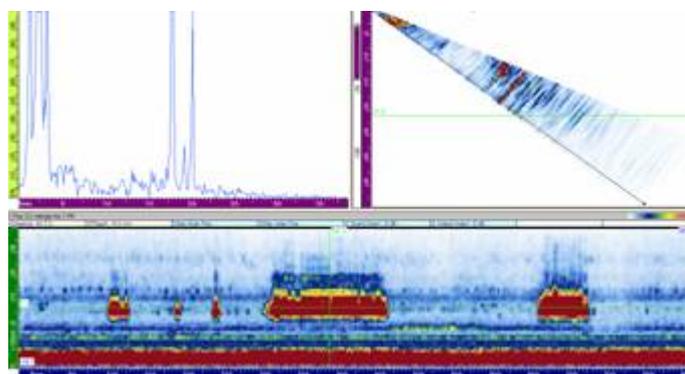


Figure 24 Phased Array Scan of 25.4 cm Diameter ERW Weld (with ID Linear Indications within the ERW)

The phased array C-scan indicates the presence of multiple linear indications within the seam of the ERW weld. The application of Sectorial scanning alone has proven to locate ID and OD indications and will provide data for accurate length determinations based on conventional dB drop techniques but has not produced the data that would allow for accurate crack depth determinations. Although the technology can be used to duplicate transducers such as the VSY 30 70 70, and the FAST, it would still be classed as a locating technique that will only provide estimates of depth.

Phased Array SCC Sizing Solutions

The accurate sizing of the detected SCC based on a diffracted wave time-of-flight approach required trials to establish the optimum focal law configuration. It has been established that

the benefits of the PA approach also include the ability to tune the array focal laws for sizing at varied depths. This potentially increases the accuracy for the defined depth range providing an additional improvement to the current practices. Ray-trace software and an advanced focal law calculator were used to help define the initial configurations.

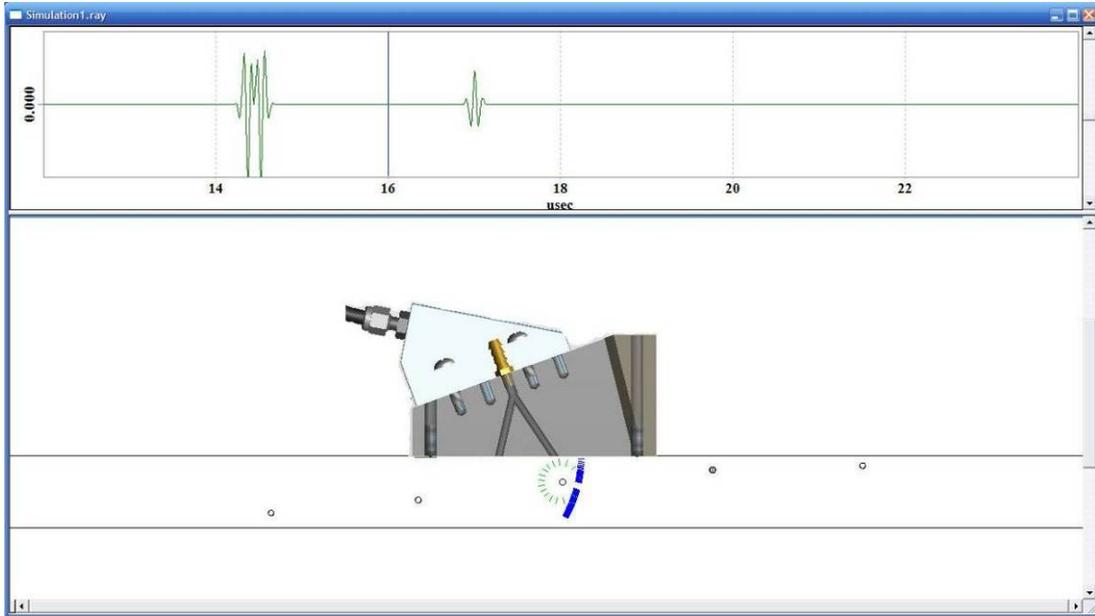


Figure 25 Ray Trace Mock-up

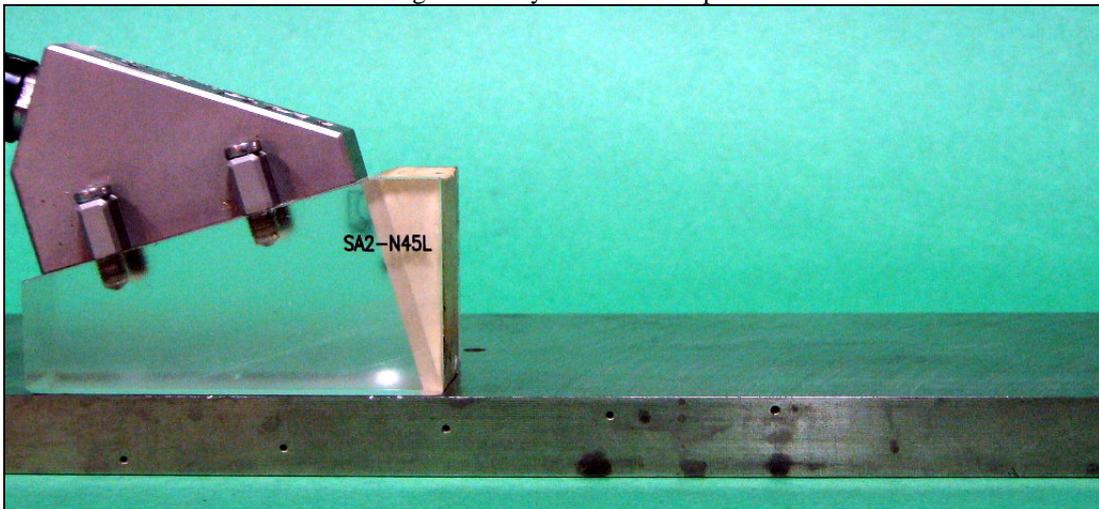


Figure 26 Side Drilled Hole (SDH) Reference Sample Used for Initial Trials

The use of the Side Drilled Holes (SDH) to provide a point source is viewed as the best option for calibrating the time-of-flight measurements. The Eclipse Thin Wall (ETW) calibration block shown also contains single and co-parallel notches to assist with other sizing approaches.

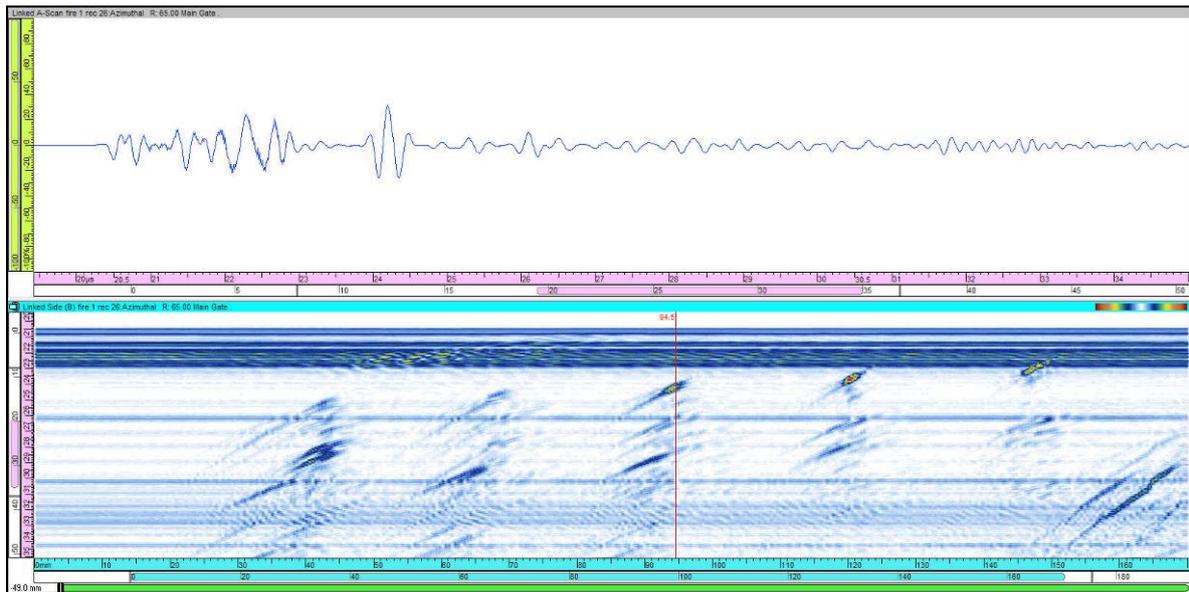


Figure 27 Transmitter and Receiver Separation Optimised for Deeper Hole Set

Summary

We have been demonstrating for more than five years that the NSDS transducers can be used to accurately size SCC. The transducers can identify co-parallel cracks located within a few millimetres of one another that are typical of a SCC colony by using accurate time measurement techniques to produce a reliable and repeatable result. The signals obtained from the NSDS transducer are relatively strong with a good signal to noise ratio that enables operators to obtain repeatable results and report sizing measurements with a higher degree of confidence.

We are also of the opinion that while we are pleased with the results of the NSDS probes for SCC sizing, we also continue to use, as part of our investigative techniques and procedures, the more traditional UT transducers and techniques to assist in the discrimination of other defects that may also pose a threat to pipeline safety.

References

- [1] ASNT, Handbook of Nondestructive Testing, vol. 7 second edition, American Society of Nondestructive Testing, 1989
- [2] Gruber G. J., Defect Identification and Sizing by the Ultrasonic Satellite-Pulse Technique, Journal of Nondestructive Evaluation Vol. 1, No. 4, 1980
- [3] Krautkramer, J. and Krautkramer, H., Ultrasonic Testing of Materials, 4th, fully revised Edition, Springer Verlag, 1990
- [4] Ginzel R., Right Tool for The Job, Eclipse Scientific Products, Internal Paper, 2004
- [5] http://www.NDE.net/article/az/ut_idx.htm
- [6] <http://www.NDE-ed.org/EducationResources/CommunityCollege/Ultrasonics/Introduction/history.htm>
- [7] Silk, M.G. (1991), Flaw size distribution in pressure vessels and flaw detection probabilities in NDE, British J. of NDE, 33(10), 491-494.
- [8] [http://www.panametrics-ndt.com/ndt/ndt technology / detection_sizing_tech.html](http://www.panametrics-ndt.com/ndt/ndt%20technology/detection_sizing_tech.html)
- [9] Same Side Sizing of Defects Using the Near Side Detection and Sizing (NSDS) Ultrasonic Transducers, Ginzel, R.K. & Kanters, W.A., Eclipse Scientific Products Inc., July 2002
<http://www.ndt.net/article/v07n07/kanters/kanters.htm>
- [10] Portable Hand Held Crack Sizing Evolution to Phased Array, Robert Ginzel, Eclipse Scientific Products Inc., Kitchener Ontario, Canada