



## **New Criterion of Thin Film Failure of Different Organic Coatings By Shearography**

**K. Habib**

**Materials Science Laboratory**

**Department of Advanced systems, (KISR)**

**P. O. Box 24885 SAFAT, 13109 Kuwait**

**Tel:965-543-0348, Fax:965-543-0239, E-Mail:khaledhabib@usa.net**

### **Abstract**

In the present work, the temperature versus thermal deformation (strain) with respect to time, of different coating films were studied by a non-destructive technique (NDT) known as shearography. An organic coating, i.e., white Neil polish, on a metallic alloy, i.e., a carbon steel, was investigated at a temperature range simulating the severe weather temperatures in Kuwait especially between the daylight and the night time temperatures, 20-60 °C. The investigation focused on determining the in-plane displacement of the coating, which amounts to the thermal deformation (strain) with respect to the applied temperature range. Furthermore, the investigation focused on determining the thermal expansion coefficients of coatings, the slope of the plot of the thermal deformation (strain) versus the applied temperature range. In other words, one could determine, from the decreasing value of the thermal expansion coefficients of coatings, a critical (steady state) value of the thermal expansion coefficients of coatings, in which the integrity of the coatings can be assessed with respect to time. In fact, determination of critical (steady state) value of the thermal expansion coefficients of coatings could be accomplished independent of parameters, i.e., UV exposure, humidity, exposure to chemical species, and so on, normally are considered in conventional methods of the assessment of the integrity of coatings. In other words, with the technique of shearography, one would need only to determine the critical (steady state) value of the thermal expansion coefficients of coatings, regardless of the history of the coating, in order to assess the integrity of coatings. Furthermore, results of shearography indicate that the technique is very useful NDT method not only for determining the critical value of the thermal expansion coefficients of different coatings, but also the technique can be used as a 2D- microscope for monitoring the deformation of the coatings in real-time at a submicroscopic scale

**KEYWORD:** Shearography, Optical Interferometry, Thermal Expansion Coefficient, In-Plan Displacement, High Temperatures, Carbon Steel, and Organic Coating.

## **1. Introduction**

It is well established that metrological methods of coherent lights such as speckle interferometry are found very useful in measuring deformation at surfaces of different objects in various conditions<sup>[1]</sup>. However, few works of the coherent light techniques have been utilized for determining the thermo-mechanical behavior of different coatings on metallic samples thus far. In fact, the author<sup>[2-3]</sup> was first to apply the technique of speckle shearing interferometry, shearography, for measuring of the thermal expansion coefficients of different coatings on metallic samples, in a temperature range between 20-60 °C. The technique of the author is dependent on determining the in-plane displacement of the coating, which amounts to the thermal deformation (strain) with respect to the applied temperature range. Furthermore, the technique focused on determining the slope of the plot of the thermal deformation (strain) versus the applied temperature range, the thermal expansion coefficients of coatings. As a consequence, one may speculate the possibility of applying the technique of shearography for determining a critical (steady state) value of the thermal expansion coefficients of coatings in which the integrity of the coatings can be assessed with respect to time. This is a very significant step, because the thermal expansion coefficient represents a viscoelastic property, ability of elastic-flow, of solid films on solid substrates, which is normally difficult to obtain by conventional methods, i.e., dial-metric methods or strain gages<sup>[6-7]</sup>. This is because the necessary contact procedures, with the solid films, of the conventional methods as compared to the non-contact procedures of the technique of shearography. In other words, a successful attempt to obtain the thermal expansion coefficients of thin films on substrates, for the first time, by the technique of shearography would lead to the exclusion of independent variables such as exposure to different chemical species (gases or liquids), humidity, and exposure to ultra violet (UV) radiation, of the study of coating behavior in the surrounding environment. As a result, the only independent variable of the study of coating deterioration by the surrounding environment becomes the aging of the coating (time). By determining the thermal expansion coefficients of coatings, ability of elastic-flow, by the technique of shearography, at a temperature range from 20-60 °C, with respect to the aging of the coatings, it is expected that the thermal expansion coefficients of coatings eventually will attain a steady state (critical) value. The critical value of the thermal expansion coefficients will become even more important with time, as the mechanical properties of coatings change, leading to the brittleness of the coatings<sup>[6-7]</sup>. Consequently, it is expected that the coatings will fail by crazing either in the film matrix or at the interface between the film and the substrate.

In this investigation, procedures of determination the critical (steady state) value of the thermal expansion coefficients of different organic coatings are described. In other words, one could determine, from the decreasing value of the thermal expansion coefficients of coatings, a critical (steady state) value of the thermal expansion coefficients of coatings, in which the integrity of the coatings can be assessed with respect to time, at a ranged of temperature, from 20 to 60 °C.

## 2. Theoretical Analysis

In speckle metrology, it is well known that an interferogram of an object normally results from two speckle wave fronts nearly superimposed but having slightly phased shift because of the deformation which usually takes place at the object surface between the first and second exposure. In the case of measuring surface relief of a coating, which associated with localized heat impingement, the following procedures are applied [2-3]:

1. Introducing localized heat impingement, of a heat source such as a hot air blower, with known diameter,  $d$ , to the coating surface of metallic samples.
2. Subsequently, a surface relief,  $\Delta d$ , is expected to occur around the area of the localized heat impingement because of the heat induction to the coating, see Fig. 1.
3. The strain relief,  $\varepsilon = \Delta d/d$ , is measured by the technique of shearography according to the Following relationship<sup>[4]</sup> :

$$\varepsilon = \frac{\lambda}{2S} \frac{N_1(1 + \cos\theta_2) - N_2(1 + \cos\theta_1)}{\sin\theta_1(1 + \cos\theta_2) - \sin\theta_2(1 + \cos\theta_1)} \quad \text{Eq.(1)}$$

Where,  $N_1, N_2$  are the fringe orders, corresponding to illumination angles  $\theta_1, \theta_2$ , respectively in which  $\theta_1, \theta_2$  are obtained from the experimental set up.  $\lambda$  is the wavelength of the laser light used, ( $\lambda = 0.6238 \mu\text{m}$  of a He-Ne laser light).  $S$  is the constant related to the shearing camera, ( $S=10 \text{ mm}$ ). For more details on the derivation of Eq. 1, the reader is encouraged to refer to the literature elsewhere [4].

4. A relationship between strain relief,  $\varepsilon$ , and the temperature range,  $\Delta T$  ( $\Delta T = 20-60 \text{ }^\circ\text{C}$ ), induced by the localized heat impingement is defined as follows [5]:

$$\varepsilon = \alpha (\Delta T) \quad \text{Eq.(2)}$$

Where,  $\alpha$  is the thermal expansion of the coating,  $\Delta T$  is the temperature range around the localized heat impingement. As a result, one can determine from Eqs. (1) and (2), the thermal expansion coefficient of coatings by shearography, by obtaining the slope of the plot of the temperature versus the strain of the coated samples.

5. A critical value of the thermal expansion coefficient of coatings can be determined from the following proposed failure criterion of a thin coating film on a solid substrate:

$$\lim_{\alpha_c \rightarrow \alpha_s} (\alpha_c / \alpha_s) = 1 \quad \text{Eq. (3)}$$

where

$\alpha_c$  is the thermal expansion coefficient of a thin coating film, assuming that  $\alpha_c$  is decreasing with time according to the literature<sup>[6-7]</sup>.

$\alpha_s$  is the thermal expansion coefficient of a solid substrate, assuming that  $\alpha_s$  is a constant.

Eq.3 represents the failure criterion of a thin coating film on a solid substrate. The relationship of Eq.3 states that as the value of the thermal expansion coefficient of the thin coating film ( $\alpha_c$ ) decreases compared to the value of the thermal expansion coefficients of the solid substrate ( $\alpha_s$ ) with respect to time, it is expected that the coating will fail by crazing either in the film matrix or at the interface between the film and the substrate.

### 3. Experimental Works

Uncoated and coated metallic samples of a carbon steel, UNS No. 1020, were used in this investigation. The chemical composition of the carbon steel is 0.18-0.23% C, 0.3-0.6% Mn, and Balanced Fe. The carbon steel samples were fabricated in a rectangular form with dimensions of 5cm X 10cm X 0.15cm. Then, some samples were covered by different coatings. The coatings were white, and gold Neil polishes. All samples were covered by the different coatings except one side of the samples. The reason behind leaving one side of the samples uncovered is because to heat the uncovered side in a furnace, while testing the painted side of the samples against high temperature. In addition to the above coated samples, uncoated samples of the carbon steel were used in this

investigation, as reference samples, for comparison sake with the coated samples. The temperature of the furnace was monitored by a digitized thermocouple and a temperature controller. The source of the heat was a hot air blower. The hot air blower was fabricated in a way to be synchronized, to reach a desired temperature in a certain time and shut down. At the desired temperature, i.e., 20, 30, 40, 50, 60 °C, a shearograph of the sample was recorded using a shearographic Camera. In this study, a shearographic camera with a T.V monitoring system were used to facilitate recordings of the real time-shearographs of the samples during the high temperature test. The optical set up for the shearographic system was based on a typical Michelson interferometry set up<sup>[2]</sup> for recordings shearographs, in which one mirror was used to introduce the shearing element ( $S=10$  mm) to the original image of the sample and the other mirror was used to introduce the phase shift to the subsequent images of the sample, see Figure 2 for more detail on the set the experimental up of the shearographic system. An He-Ne laser light was used as a coherent light in this investigation. The size of the recorded shearograph was 10cm X 3.3cm. The shearographic camera is made by Steinbichler Optotechnik GmbH, in Germany. Finally, the obtained shearographs of the samples were interpreted to thermal deformations (strain) by using a special software package. Then the thermal expansion coefficients of the different coating were determined from the slope of the plot of the thermal deformation (strain) versus the applied temperature range. In addition, the relationship of Equ.3, of the ratio of  $\alpha_c/\alpha_s$  versus time, were plotted for different coatings, in order to show the safe and unsafe regions of the failure criterion of a thin coating film on a solid substrate.

#### 4. Results and Discussion

Figures 3, 4, 5, 6, and 7 illustrate examples of shearographs of uncoated carbon steel sample at 20, 30, 40, 50, 60 °C, respectively. It is obvious from the shearographs that the magnitude of the strain bar is ranged from 0-2.66 X100  $\mu\text{m}/\text{mm}$  (0.0-0.266% strain), from the black color (at zero strain) to the white color (at 2.66 X100  $\mu\text{m}/\text{mm}$ ). Each color on the strain bar represents an increment of a strain magnitude equivalent to 0.33 X100  $\mu\text{m}/\text{mm}$  (0.033% strain). Fig.3 represents a shearograph of the uncovered carbon steel at 20 °C, at room temperature, without any thermal deformation, at the beginning of the test. It is clear from Fig.3 that the sample of the uncoated carbon steel has not been subjected to any thermal deformation, because there is no color contrast existed in the shearograph, due to a thermal deformation. In contrast, Fig.4 shows the uncovered sample of the

carbon steel at 30 °C, in which the pink-red color is uniformly dominating the shearograph. In other words, Fig. 4 has been subjected to a thermal deformation ranged from 1.0- 1.33 X100  $\mu\text{m}/\text{mm}$  (0.1-0.133% strain). Furthermore, Fig.4 shows the uncovered sample of the carbon steel at 40 °C in which the light blue-pink color is uniformly dominating the shearograph with some spots of red color. This means, Fig.5 has been subjected to a thermal deformation ranged from 0.33- 1.33 X100  $\mu\text{m}/\text{mm}$  (0.033-0.133% strain). Also, Fig.6 shows the uncovered sample of the carbon steel at 50 °C in which the pink-red color is uniformly dominating the shearograph with some spots of green color. This means, Fig.6 has been subjected to a thermal deformation ranged from 1.00- 1.66 X100  $\mu\text{m}/\text{mm}$  (0.1-0.166% strain). In addition, Fig. 7 shows the uncovered sample of the carbon steel at 60 °C, in which red-green color is dominating the shearograph. In other words, Fig. 7 has been subjected to a thermal deformation ranged from 1.33- 1.66 X100  $\mu\text{m}/\text{mm}$  (0.133-0.166% strain), in a homogeneous manner. In general, from shearographs in Figs. 3-7 one can conclude that the uncovered sample of the carbon steel has gone through a thermal deformation ranged from 0-1.66 X100  $\mu\text{m}/\text{mm}$ , with an average thermal expansion coefficient equivalent to  $\text{Ave.}\alpha_{cs}=0.025 \text{ X100 } \mu\text{m}/\text{mm } ^\circ\text{C}$ , in a temperature ranged from 20-60 °C, see Figure 8, for the plot of the temperature versus the strain of the carbon steel sample.

In a similar fashion to the above, the average thermal expansion coefficients of carbon steel samples covered by the white Neil polish was determined, see Figure 9, for the plot of the temperature versus the strain of the carbon steel covered by the white Neil polish. The average thermal expansion coefficient of the white Neil polish was found equivalent to  $\text{Ave. } \alpha_{wnp} = 0.038 \text{ X100 } \mu\text{m}/\text{mm } ^\circ\text{C}$ , in a temperature ranged from 20-60 °C. Furthermore, a relationship of the ratio of  $\alpha_{wnp}/\alpha_{cs}$  versus time, using Equ.3, was plotted, see Fig.10, in order to show the safe (above the line) and unsafe (below the line) regions of the failure criterion of the white Neil polish on the carbon steel substrate. Fig.10 was plotted based on  $\alpha_{wnp}/\alpha_{cs}=1.52$ , at (time)  $T=0$  month and  $\alpha_{wnp}/\alpha_{cs}=1.00$ , at  $T=24$  months, assuming that the failure of the coating will occur within 24 months of the coating exposure to the surrounding environment.

Also, in a similar manner to the above, the average thermal expansion coefficients of carbon steel samples covered by the gold Neil polish was determined, see Figure 11 for the plot of the temperature versus the strain of the carbon steel covered by the gold Neil polish. The average thermal expansion coefficient of the gold Neil polish was found equivalent to  $\text{Ave. } \alpha_{gnp} = 0.046 \text{ X100 } \mu\text{m}/\text{mm } ^\circ\text{C}$ , in a temperature ranged from 20-60 °C.

Eventually, in similar manner to Fig.10, a relationship of the ratio of  $\alpha_{gnp}/\alpha_{cs}$  versus time was plotted, see Figs.12, in order to show the safe and unsafe regions of the failure criterion of the gold Neil polish on the carbon steel substrate. Figs.12 was plotted based on  $\alpha_{gnp}/\alpha_{cs}=1.8$  at (time) T=0month and  $\alpha_{gnp}/\alpha_{cs}=1.00$  at T =24months, assuming that the failure of the coating will occur within 24 months of the coating exposure to the surrounding environment.

## 5. Conclusions

The following conclusions have been drawn from the above investigation:

1- The results of the present investigation indicate that the technique of shearography is very useful NDT method not only for determining the critical values of the thermal expansion coefficients of different coatings, but also the technique can be used as a 2D- microscope for monitoring the deformation of different coatings in real-time at a submicroscopic scale.

2- The average thermal expansion coefficient of the uncovered carbon steel sample was determined to be equivalent to  $Ave.\alpha_{cs}= 0.025 \times 100 \mu\text{m}/\text{mm} \text{ } ^\circ\text{C}$ , in a temperature ranged from 20-60  $^\circ\text{C}$ .

3- The average thermal expansion coefficients of the carbon steel samples covered by the white and the gold Neil polishes were determined to be  $Ave.\alpha_{wnp}=0.038 \times 100 \mu\text{m}/\text{mm} \text{ } ^\circ\text{C}$ , and  $Ave. \alpha_{gnp} = 0.046 \times 100 \mu\text{m}/\text{mm} \text{ } ^\circ\text{C}$ , respectively, in a temperature ranged from 20-60  $^\circ\text{C}$ , see Figs 9, 11, for the plots of the temperature versus the strain of the carbon steel sample covered by the white and gold Neil polishes.

4- For the first time, the ratio of  $\alpha_{wnp}/\alpha_{cs}$ ,  $\alpha_{gnp}/\alpha_{cs}$ , versus time were plotted, see Figs.10, and 12, respectively, in order to show the safe (above the line) and unsafe (below the line) regions of the failure criterion of the white and the gold Neil polishes on the carbon steel substrate. Figs.10 and 12 were plotted based on  $\alpha_{wnp}/\alpha_{cs}=1.52$ , and  $\alpha_{gnp}/\alpha_{cs}=1.8$ , at (time) T=0month and  $\alpha_{wnp}/\alpha_{cs} = 1$  and  $\alpha_{gnp}/\alpha_{cs}=1$  at T =24months'.

5- It is worth mentioning that the plots of Figs.10 and 12 are based on a conservative approach. Plots such as those of Figs.10 and 12 based on a practical (less conservative) approach can be obtained by

determining the ratio of  $\alpha_c/\alpha_s$  of a coated carbon steel, once a month during the 24 months period of the exposure to the surrounding environment. This will be the next task of the present investigation.

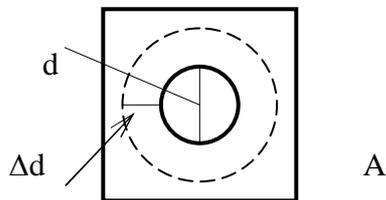


Fig.1 Localized heat impingement ,d , and the surface relief,  $\Delta d$ , which associated with the heat induction to the surface area of the coating, A.

## 6-REFERENCES

- [1]-K. Robert, ERF, “Speckle Metrology”, Academic Press, New York (1978), P. 2.
- [2] K.Habib,”Thermally induced deformations measured by shearography”, *Optics and Laser Technology*. Vol.37, pp. 509-512 (2005).
- [3]-K.Habib,” Measurement of Thermal Expansion Coefficients of Thin Film of Different Organic Coatings by Shearography “,Key Engineering Materials, Vol.321-323,PP.67-70( 2006).
- [4]-H.Zhang and J.Ke,“Determination of Residual Stress by Laser Speckle Shearing Interferometry and Hole Drilling Method” Journal of Experimental Mechanics(1986),Vol. **1**, pp.181-188.
- [5]-J.Shigley, “Mechanical Engineering Design”, McGraw-Hill 3<sup>rd</sup> Edition, New York (1978),pp.67-69.
- [6]-R.Lambourne, ”Paint and Surface Coatings: Theory and Practice”, John Wiley& Sons (1987).
- [7]-P.Schweitzer, ”Mechanical and Corrosion Resistance Properties of Plastics and Elastomers”, Marcel Dekker Inc., New York. (2000).


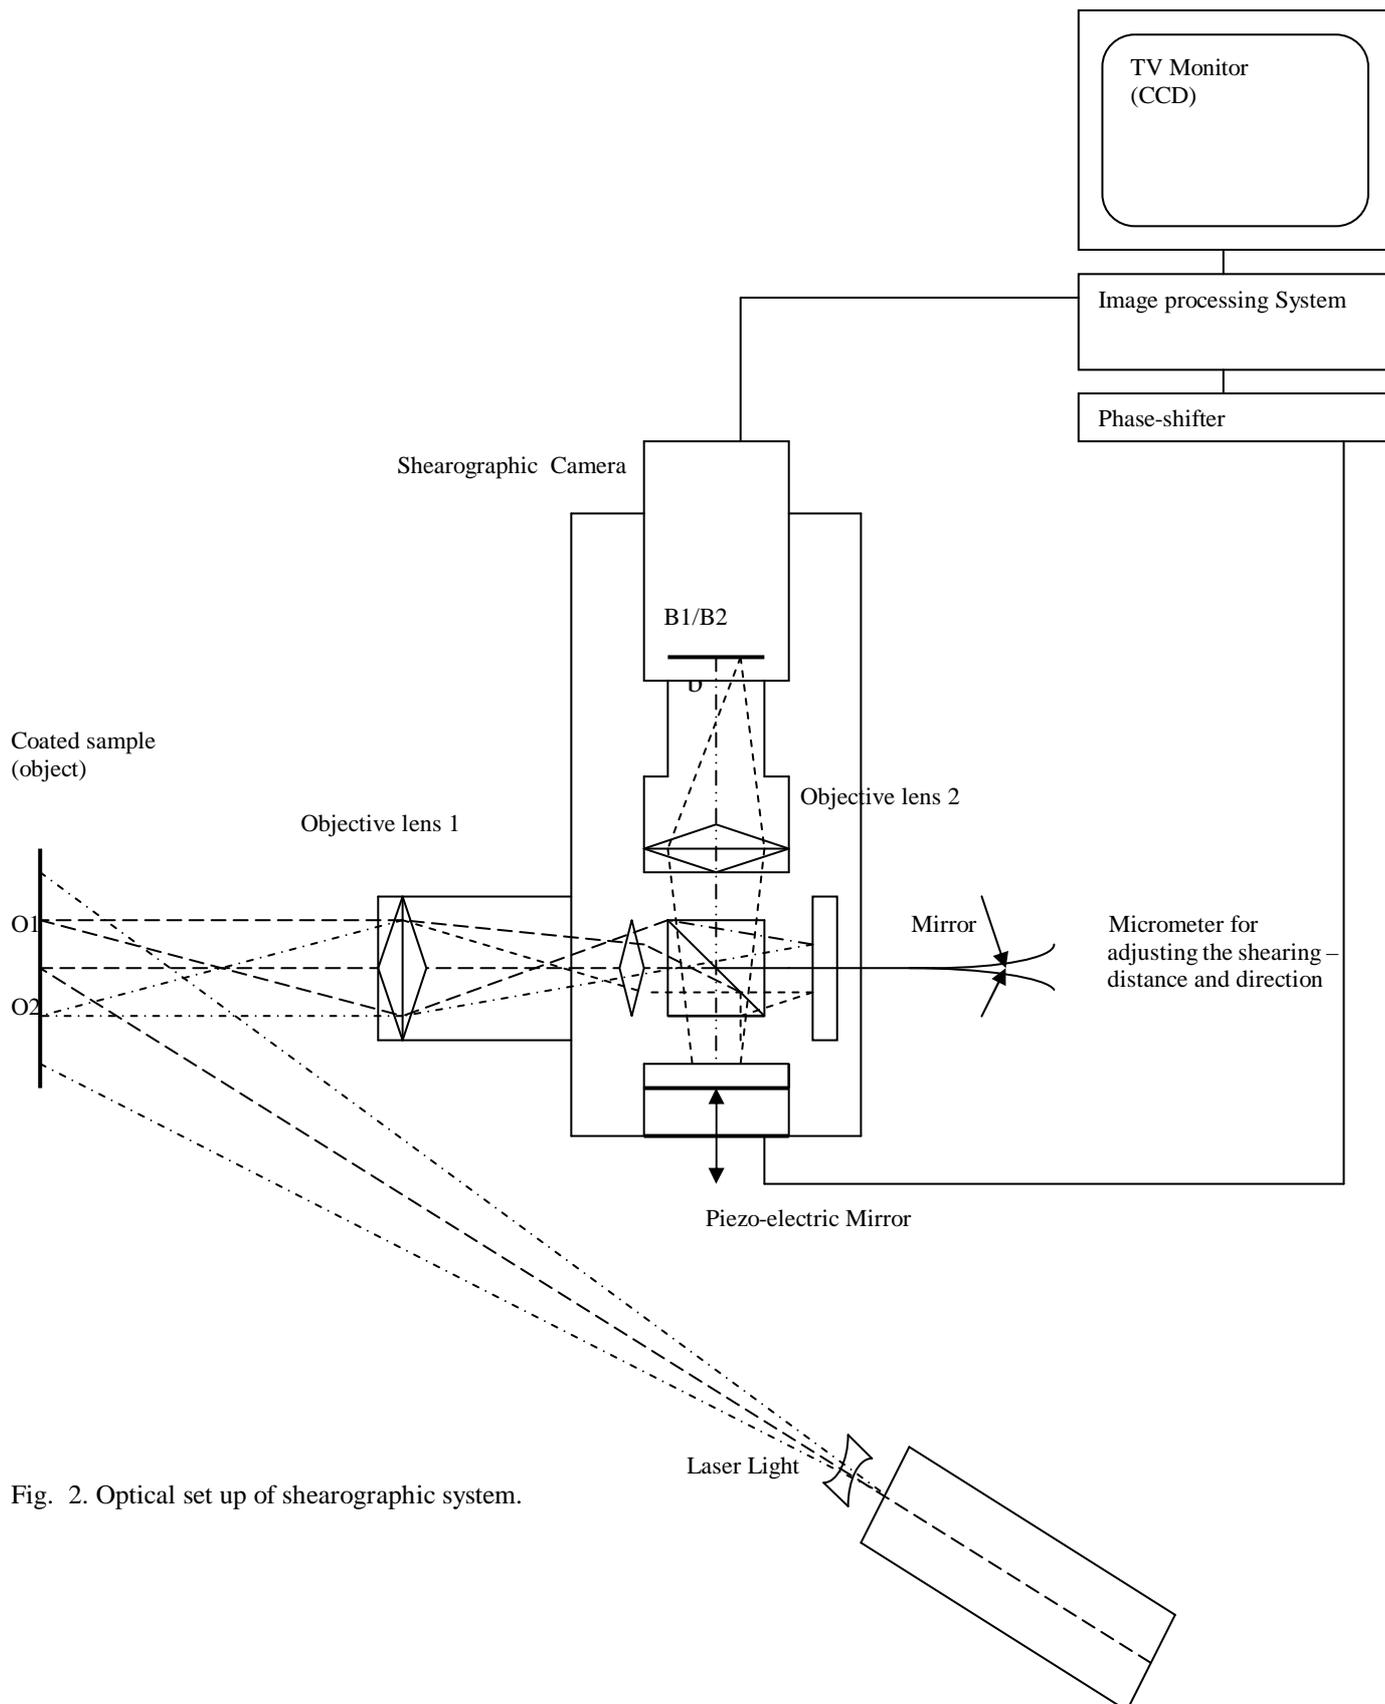


Fig. 2. Optical set up of shearographic system.

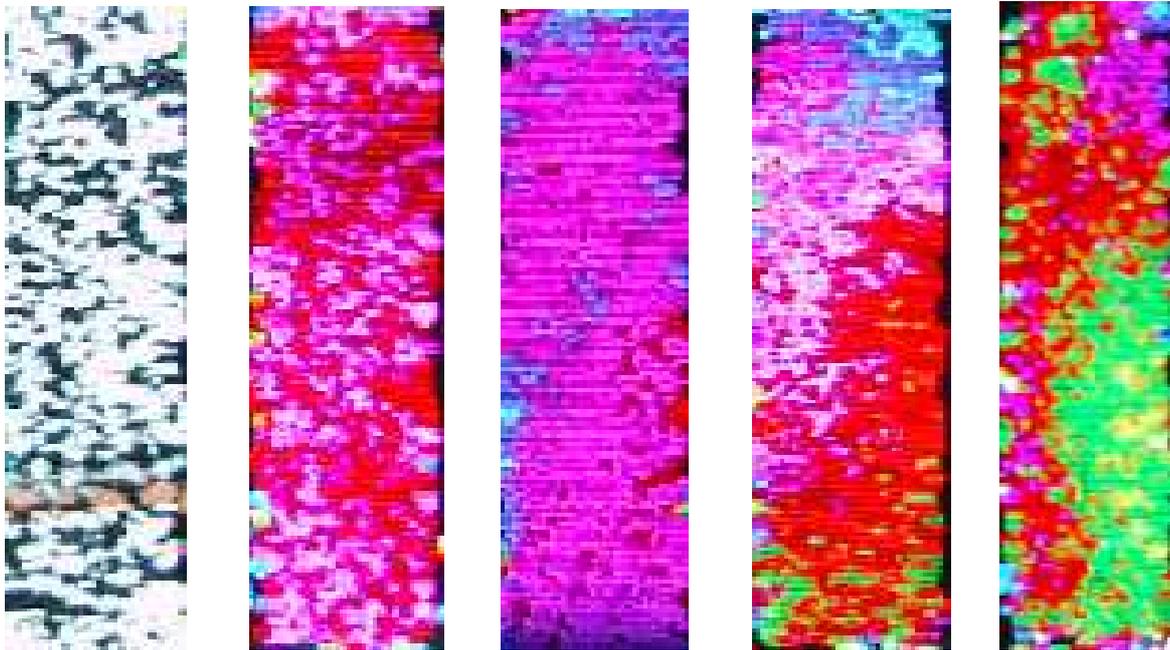

3

4

5

6

7

Figs.3,4,5,6,7 Show 2D-shearographs of the uncoated carbon steel sample at a temperature around 20 °C,30 °C,40 °C, 50 °C,and 60 °C, respectively.

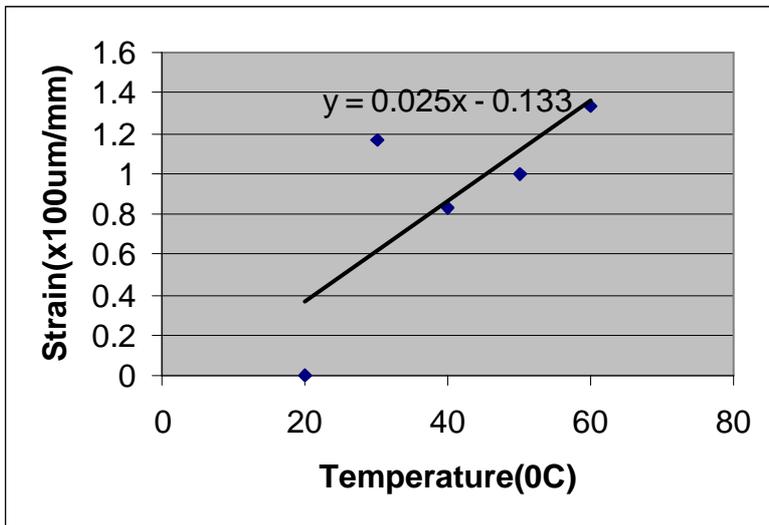


Fig 8 shows a plot of the temperature versus the strain of the carbon steel sample.

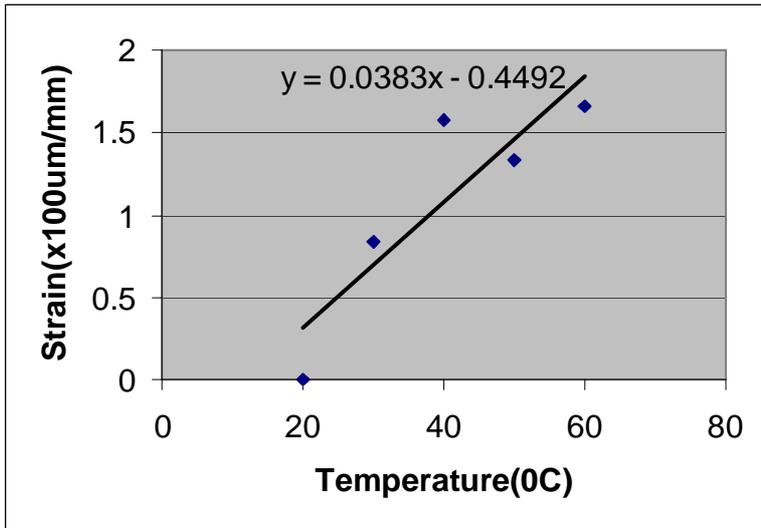


Fig.9 shows a plot of the temperature versus the strain of the carbon steel sample covered by the white Neil polish.

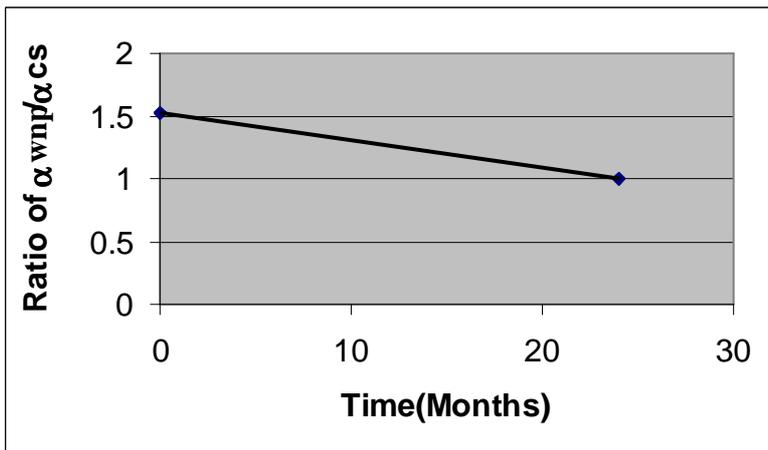


Fig.10 shows a relationship of the ratio of  $\alpha_{wnp}/\alpha_{cs}$  versus time, using Equ.3, of the failure criterion of the white Neil polish, on the carbon steel substrate.

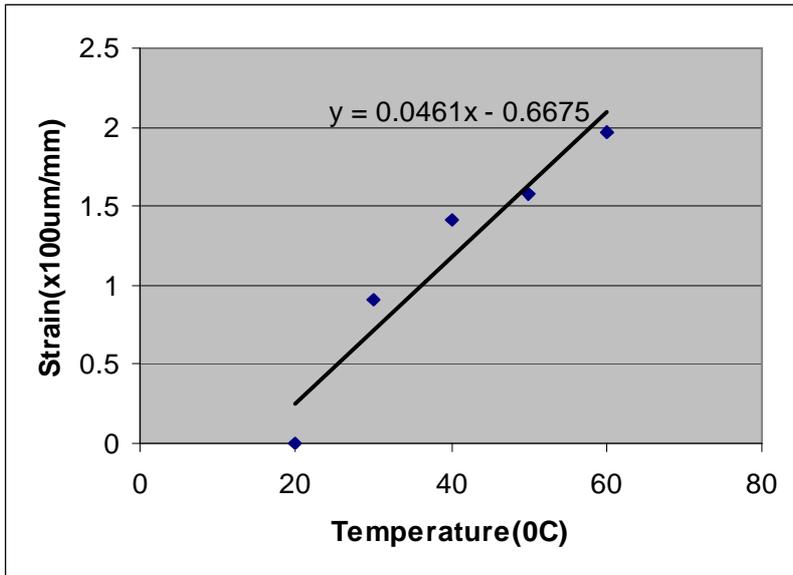


Fig.11 shows a plot of the temperature versus the strain of the carbon steel sample covered by the gold Neil polish.

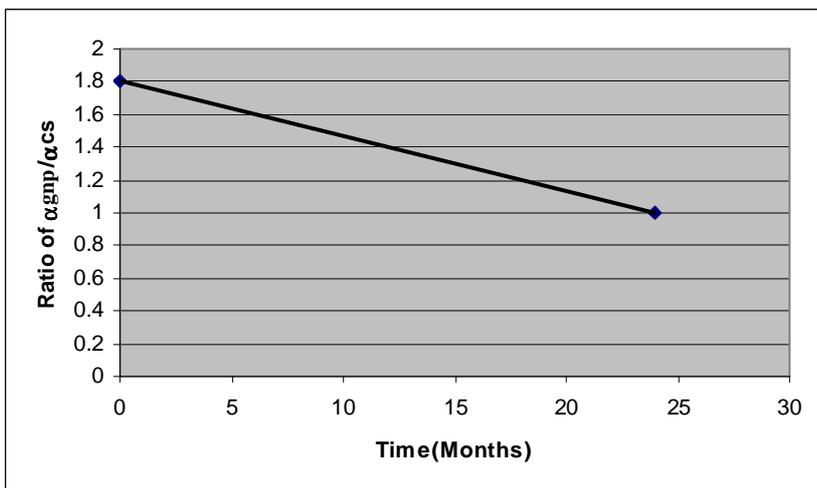


Fig.12 shows a relationship of the ratio of  $\alpha_{gnp}/\alpha_{cs}$  versus time, using Equ.3, of the failure criterion of the gold Neil polish on the carbon steel substrate.